

Effect of metal-ion doping on the characteristics and photocatalytic activity of TiO₂ nanotubes for the removal of toluene from water

Rongfang Yuan, Beihai Zhou, Duo Hua, Chunhong Shi and Li Ma

ABSTRACT

Toluene is an extensively used reagent that could cause water pollution and endanger human health. In this work, an O₃/UV/ion-doped TiO₂ nanotubes process was investigated to obtain the optimum TiO₂ nanotubes for effective toluene decomposition. Photocatalytic activity is found to be influenced by the doped-ion type by affecting the ionic radius, valence state, and configuration of the dopant. The calcination temperature and doping concentration, which change the weight fractions of the anatase phase (f_A), the Brunauer–Emmett–Teller surface area (S_{BET}), and the energy band gap (E_g) of the catalyst, also affect the photocatalytic activity. When TiO₂ is doped with ions, S_{BET} decreases and E_g becomes narrower. The photocatalytic activities of TiO₂ for toluene removal increase after doping with Ag⁺, Al³⁺, Cu²⁺, Fe³⁺, Mn²⁺, Ni²⁺, V⁵⁺, and Zn²⁺. Moreover, the 1.0% Fe³⁺-doped TiO₂ nanotubes calcined at 550 °C have the highest catalytic activity, with a toluene removal efficiency of 70.7%.

Key words | ion-doping, mechanism, TiO₂ nanotubes, toluene, UV photocatalytic ozonation

Rongfang Yuan

Beihai Zhou (corresponding author)

Duo Hua

Chunhong Shi

Department of Environmental Engineering,
School of Civil and Environmental Engineering,
University of Science and Technology Beijing,
No. 30 Xueyuan Road,
Beijing 100083,
China
and

Key Laboratory of Educational Ministry for High
Efficiency Mining and Safety in Metal Mines,
University of Science and Technology Beijing,
Beijing 100083,
China
E-mail: zhoubeihai@sina.com

Li Ma

PetroChina Huabei Petrochemical Company,
Renqiu,
Hebei 062552,
China

INTRODUCTION

Toluene is extensively used for the preparation of many compounds, such as benzaldehyde, benzyl alcohol, benzoic acid, and chloro derivatives; it is also used as base chemicals to synthesize dyes, pigment inks, explosives, and medicines (Takeuchi *et al.* 2012). These applications cause water pollution and endanger human health.

Several techniques have been developed to treat toluene. One of which is ultraviolet (UV) photocatalytic ozonation that is highly efficient in generating •OH for the degradation of pollutants (Lin & Lin 2007).

Choosing the appropriate photocatalyst is essential for removing toluene, and TiO₂ is a good candidate. TiO₂-photocatalyzed reactions are non-selective oxidation processes in mg/L level, and the use of TiO₂ is effective for inactive substrates (Carp *et al.* 2004). Moreover, the presence of TiO₂ can provide additional nuclei for bubble formation, thereby enhancing the degradation of pollutants (Adewuyi 2001).

Compared with the powder form, TiO₂ nanotubes have a larger specific surface area. This surface area increases the available Brunauer–Emmett–Teller (BET) surface area (S_{BET}) for the separation of electron-hole pairs and

subsequently enhances electron transfer, as well as the interpenetration of holes (Pang & Abdullah 2012a). However, the relatively wide band gap of TiO₂ (3.2 eV) limits the efficiency of photocatalytic reactions because of the high recombination rate of photogenerated electrons and holes (Sun *et al.* 2009). Metal ion-doped TiO₂ nanotubes have been studied to solve this problem (Pang & Abdullah 2012b). Nevertheless, to the best of our knowledge, most studies have focused on the photocatalytic degradation of gaseous toluene, and no study has reported on the application of O₃/UV/ion-doped TiO₂ nanotubes for the removal of toluene from water.

In this work, we investigated the effect of metal-ion doping on the photocatalytic activity of TiO₂ nanotubes in removing toluene through the O₃/UV method. Eight types of metal ions were investigated, namely, Ag⁺, Al³⁺, Cu²⁺, Fe³⁺, Mn²⁺, Ni²⁺, V⁵⁺, and Zn²⁺, and Fe³⁺ elicited optimum results. Characteristic analyses of the TiO₂ nanotubes were implemented to reveal the influencing factors on the photocatalytic activities of the catalysts (Zwilling *et al.* 1999). In addition, control experiments

were conducted to investigate the effects of O₃, UV, and UV/Fe³⁺-doped TiO₂ processes for toluene removal, and the mechanism of the O₃/UV/Fe³⁺-doped TiO₂ process was discussed.

METHODS

Material

P-25 TiO₂ was provided by the Degussa Corporation (Richfield Park, New Jersey). The powder has an S_{BET} of 50 m²/g, an average crystallite size of 21 nm, and a crystal structure of 80% anatase and 20% rutile. Toluene, AgNO₃, AlCl₃, CuCl₂·2H₂O, Fe(NO₃)₃·9H₂O, Mn(NO₃)₂·4H₂O, NiCl₂, NH₄VO₃, and ZnCl₂ (A.R.) were purchased from the Beijing Chemical Reagent Company.

A photocatalytic reactor (60 mm in diameter and 750 mm long), equipped with a 37 W 254 nm UV lamp, was purchased from Haili Lighting Equipment Company (Beijing) and was used in the experiment.

Preparation of TiO₂ nanotubes

One gram of P-25 TiO₂ was added to a 16 mL of a 10 mol/L NaOH solution in a Teflon vessel. The mixture was stirred for 2 h at room temperature, heated at 110 °C for 24 h in an oven, and cooled to room temperature in air. The as-prepared precipitate was washed with distilled water until the pH was 7, and was subsequently dispersed in a 0.1 mol/L HCl aqueous solution (0.1 mol/L HNO₃ solution for Ag⁺-doping). The precipitate was ultrasonicated for 30 min, washed until the pH was 7, and then dried at 60 °C. The nanotubes were prepared by calcining the precipitate at 550 °C for 2 h. In these reactions, NaOH initially disturbed the crystalline structure of P-25 TiO₂. The free octahedra reassembled and linked together, and then the anatase phase grew longitudinally. The lateral growth led to the formation of two-dimensional crystalline sheets. The crystalline sheets rolled up and decreased the total energy, thereby saturating the dangling bonds and reducing the specific area, and resulting in the formation of TiO₂ nanotubes (Wang *et al.* 2004).

The ion-doped TiO₂ nanotubes were prepared based on the above procedure except that metal salts were doped at 1.0% (atomic concentration). The metal salts used as precursors for dopant ions were AgNO₃, AlCl₃, CuCl₂·2H₂O, Fe(NO₃)₃·9H₂O, Mn(NO₃)₂·4H₂O, NiCl₂, NH₄VO₃, and ZnCl₂.

Characterization of TiO₂ nanotubes

X-ray diffraction (XRD) patterns were collected by a Rigaku Dmax-RB diffractometer (Tokyo, Japan). The surface elemental composition of TiO₂ was recorded by an X-ray photoelectron spectroscopy (XPS; AXIS ULTRA^{DL}, Kratos Analytical, UK). Transmission electron microscopy (TEM) images were obtained by a HITACHI HT-7700 electron microscope (Tokyo, Japan). S_{BET} was measured by Quadrasorb SI-MP apparatus (Quantachrome Instruments, USA). Diffuse reflectance spectroscopy (DRS) analyses were performed using a HITACHI U-3010 UV-vis scanning spectrophotometer (Tokyo, Japan).

The weight fractions of the anatase in anatase-rutile mixtures in the samples (*f_A*) were calculated by Equation (1) (Spurr & Myers 1957) based on the XRD patterns of the catalyst.

$$f_A = \frac{1}{1 + 1.265 \frac{I_R}{I_A}} \quad (1)$$

where *I_R* and *I_A* are the maximum XRD peak intensity of the rutile phase (110) and the anatase phase (101).

The UV-vis DRS analysis of the catalysts were conducted to obtain the energy band gaps (*E_g*). TiO₂ nanotubes had an indirect band gap, and relationship plots were used:

$$F(R_\infty)h\nu = A(h\nu - E_g)^2 \quad (2)$$

where *F(R_∞)* is the Kubelka–Munk (K–M) function, *h* is the Planck constant, and *ν* is the frequency. The value of *F(R_∞)* can be estimated using the K–M formula:

$$F(R_\infty) = K/S = \frac{(1 - R_\infty)^2}{2R_\infty} \quad (3)$$

where *R_∞* is the diffuse reflectance.

Photocatalytic activity tests

Aqueous slurries were prepared by adding 0.15 g of TiO₂-based photocatalyst to 1,500 mL of 2.25 mg/L toluene aqueous solution with a pH of 7. The aqueous slurries were stirred and bubbled with O₃ (1 L/min, 10%) and irradiated with a 254 nm UV lamp. Every 10 min, a 200 mL sample was acquired. The toluene concentrations were analyzed through the solvent extraction-capillary gas chromatography

method (GB/T 5750.12-2006, China), and a GC-FID gas chromatograph (Agilent 7890A, USA) was used. The temperatures of the injector and the FID (flame ionization detector) of GC were 210 and 220 °C, respectively. The temperature program comprised two phases: the temperature was set at 50 °C for 10 min initially, and then ramped up to 80 °C at a rate of 10 °C/min and held for 3 min.

RESULTS AND DISCUSSION

Characterization of photocatalysts

Morphology of the catalysts

The TEM image of 550 °C calcined Fe³⁺-doped TiO₂ nanotubes (Figure 1(a)) shows that the nanotubes were successfully synthesized. Moreover, other ion-doped nanotubes share a similar morphology. The Fe³⁺-doped TiO₂ nanotubes have an average diameter of approximately 8 nm with a hollow and open-ended structure.

XRD analysis

XRD patterns and the f_A of the TiO₂ nanotubes are shown in Figure 1(b) and Table 1. Anatase and rutile phases in TiO₂ nanotubes existed. The characteristic peaks of the (101) crystal plane of anatase and the (110) crystal plane of rutile were located at about 25.3° and 27.4°, respectively. Compared with those of undoped TiO₂, the Bragg angles of the (101) peak position of the ion-doped TiO₂ shifted to lower angles, and the anatase peak intensities decreased. These results occurred because the crystallite has numerous crystal planes caused by ion doping; thus, such crystallite cannot be considered as an ideal crystal. Furthermore, the dopant ions substitute Ti⁴⁺ in the lattice, which resulted in the deformation of the crystal lattice. Therefore, broadening diffraction peak and decreasing peak intensity were observed. Among the dopant ions, only Ag⁺ is observed in the XRD patterns in the form of Ag₂O based on the characteristic peak of the (111) crystal plane of Ag₂O at 32.8° and the XPS spectra of Ag 3d; this result is attributed to the difficulty of Ag⁺ in entering the TiO₂ lattice (Epifani *et al.* 2000). Other ions are partially dispersed in the bulk of TiO₂ nanotubes (Pang & Abdullah 2012b). The metallic oxides from other doped ions may also be formed on the surface of TiO₂. However, these oxides are not observed in the XRD patterns because their metal sites are below

the visibility limit of X-ray analysis (Ravichandran *et al.* 2009).

XPS analysis

XPS analysis was performed to determine the surface composition and the chemical state of the elements in the catalysts. The binding energies of Ag 3d, Al 2p, Cu 2p, Fe 2p, Mn 2p, Ni 2p, V 2p, and Zn 2p (Table 1) for 550 °C calcined catalysts indicate that the doping ions existed as Ag⁺, Al³⁺, Cu²⁺, Fe³⁺, Mn²⁺, Ni²⁺, V⁵⁺, and Zn²⁺ in the lattice. The binding energies from 458.15 to 459.65 eV for the TiO₂ nanotubes correspond to the peaks of Ti 2p_{3/2}, whereas those from 464.05 eV to 464.70 eV correspond to Ti 2p_{1/2}, thereby indicating that Ti existed as Ti⁴⁺. The Ti 2p binding energy of the ion-doped TiO₂ nanotubes increased compared with that of the pure TiO₂ because the electrons in the conduction band of the TiO₂ may have transferred to the doped metal ions on the surface of the TiO₂, which resulted in a decrease in the outer electron cloud density of the Ti ions (Li *et al.* 2011). Compared with the binding energies of the Ti 2p for the 550 °C calcined ion-doped TiO₂, the binding energies for the 60 °C calcined ion-doped TiO₂ increased insignificantly. This result indicates the formation of Ti–O–(doping-ion) bonds in the crystal lattice during calcination.

The oxygen groups in the spectra of O 1s (Figure 1(c)) for the 550 °C calcined catalysts are distributed in the form of crystal lattice oxygen (O²⁻), which is in accordance with the binding energies from 529.9 to 530.9 eV. The peak located at 529.9 eV is assigned to the oxygen bound to Ti⁴⁺ (TiO₂) (Leinen *et al.* 1996). Moreover, the O 1s binding energy of the ion-doped TiO₂ nanotubes increased, unlike that of the pure TiO₂.

Surface area analysis

The catalytic efficiencies of TiO₂ nanotubes are related to the S_{BET} of the catalyst (Zhang *et al.* 2012). A larger S_{BET} benefits the adsorption of pollutants on the surface of TiO₂ where the pollutants are degraded by O₃, and more areas are supplied for electron-hole pair separation. The S_{BET} of ion-doped TiO₂ nanotubes are smaller than that of undoped TiO₂ nanotubes, particularly for Ag⁺, Mn²⁺, and Ni²⁺-doped TiO₂ nanotubes (Table 1). The S_{BET} decreases when TiO₂ is doped by ions because of the partial pore blockages and framework defects (Pang & Abdullah 2012b). The S_{BET} of the TiO₂ nanotubes is

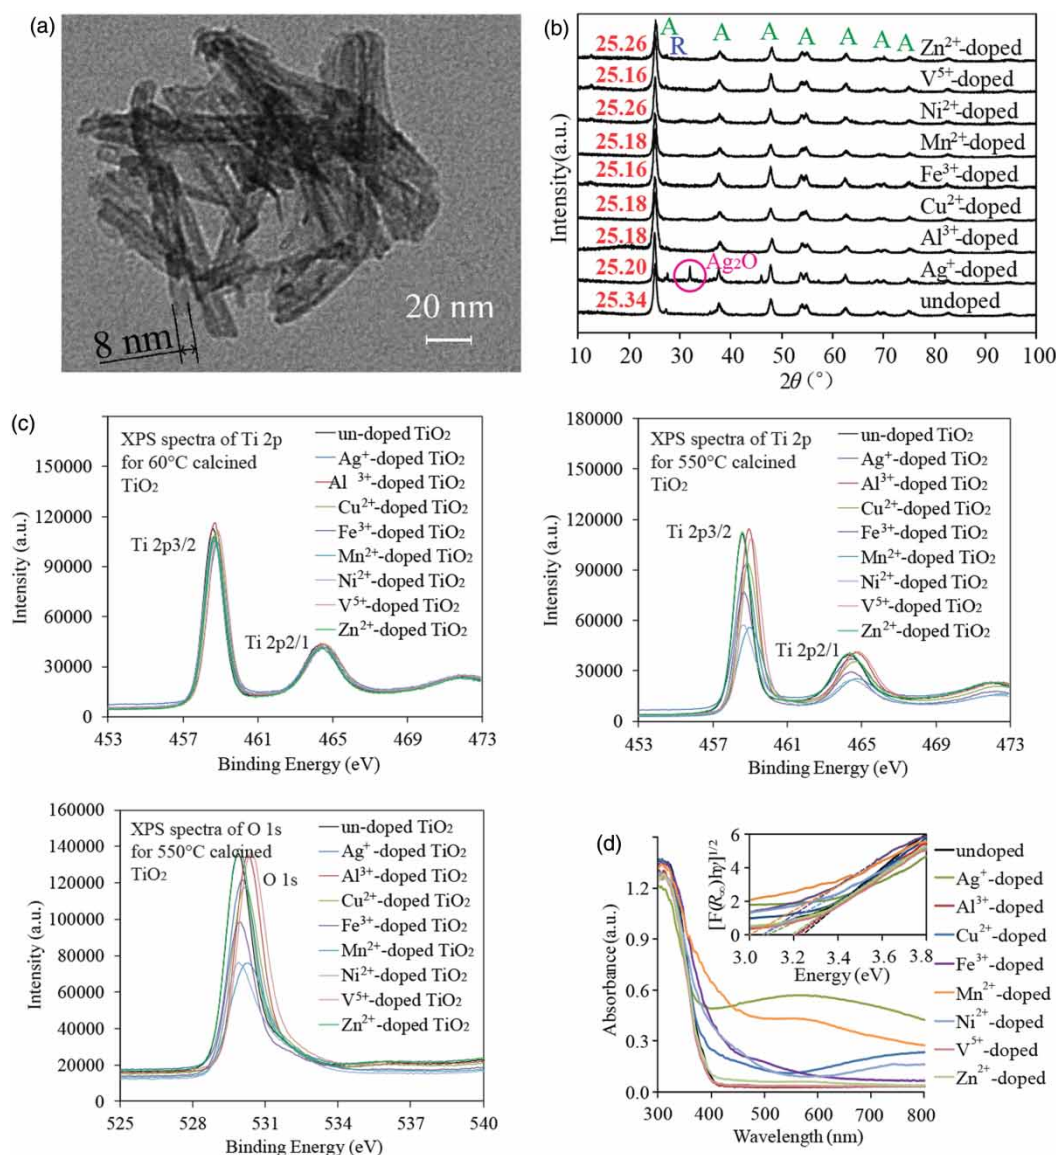


Figure 1 | Characterization of TiO₂ nanotubes. (a) TEM image of Fe³⁺-doped TiO₂; (b) XRD patterns of the catalysts; 'A' refers to the anatase phase; 'R' refers to the rutile phase; (c) XPS spectra of Ti 2p and O 1s; (d) UV-vis DRS and energy band gap of TiO₂ nanotubes.

significantly larger than that of P-25 TiO₂ because of the inner and outer surfaces of the layered-tubular structure, which is one of the special qualities of the nanotubes (Pang & Abdullah 2012a).

UV-vis DRS analysis

The reflectance spectra of ion-doped TiO₂ slightly shift toward longer wavelength (red shift) as compared with that of the undoped TiO₂, and the E_g of the ion-doped TiO₂ is visibly narrower (Figure 1(d); Table 1). This result revealed that the doped elements involved are indeed

incorporated into the lattice of the TiO₂ nanotubes; therefore, doped elements altered the crystal and electronic structures of the lattice of the TiO₂ nanotubes (Yu *et al.* 2009). The reduction in E_g of the TiO₂ nanotubes allows the excitation of the catalyst under lower power of irradiation, and thereby enhances the photocatalytic activity of the catalyst. Moreover, the ion-doped TiO₂ nanotubes display various colours depending on the type of doping-ions: Ag⁺-doped nanotubes appear in grayish, Al³⁺-doped and Zn²⁺-doped white, Cu²⁺-doped bluish, Fe³⁺-doped orange, Mn²⁺-doped pink, Ni²⁺-doped greenish, and V⁵⁺-doped yellowish. The E_g of the ion-doped TiO₂ is related to the colour

Table 1 | Catalytic properties of the catalysts

Type of catalysts	f_A (%)	Binding energy of doped ions (eV)	E_g (eV)	S_{BET} (m ² /g)
Undoped	83.4	–	3.24	123
Ag ⁺ -doped	84.6	Ag 3d 5/2 (368.3)/3/2 (374.2)	3.12	56
Al ³⁺ -doped	86.0	Al 2p (75.7)	3.22	123
Cu ²⁺ -doped	91.3	Cu 2p 3/2 (933.2)/1/2 (953.6)	3.21	99
Fe ³⁺ -doped	87.5	Fe 2p 3/2 (710.9)/1/2 (726.3)	3.06	118
Mn ²⁺ -doped	91.3	Mn 2p 3/2 (642.5)/1/2 (653.9)	3.00	61
Ni ²⁺ -doped	88.5	Ni 2p 3/2 (855.5)/1/2 (871.9)	3.06	48
V ⁵⁺ -doped	85.3	V 2p 3/2 (517.4)/1/2 (524.7)	3.20	123
Zn ²⁺ -doped	81.5	Zn 2p 3/2 (1021.8)/1/2 (1044.7)	3.19	134

of the catalyst. A darker appearance of the catalyst elicits a narrower E_g .

Photocatalytic activity of the catalysts

Influence of doping ions

Photocatalytic activity tests were conducted to investigate the effects of the dopant types on the catalytic activities of the catalysts (Figures 2(a) and 2(b)). The removal rate of toluene increases when TiO₂ nanotubes are doped by ions because the existing impurity band reduces the recombination of the photoinduced electron-hole; the photoinduced electron-hole can transfer electrons more efficiently to the oxygen adsorbed on the surface of TiO₂ nanotubes (Li *et al.* 2011). The S_{BET} , crystalline phases, crystallinity, and E_g of TiO₂ nanotubes are also crucial factors that affect the photocatalytic activity. The highest photocatalytic activity was achieved in the presence of the Fe³⁺-doped catalyst that was calcined at 550 °C, which removed 70.7% of the toluene.

The ionic radius of Ag⁺ was significantly larger than that of Ti⁴⁺ (60.5 pm). The electrons continuously transferred from TiO₂ to Ag₂O on the surface of the TiO₂, which allows the pollutant with negative charges to be easily adsorbed by the catalysts. The f_A of Ag⁺ was larger than that of the undoped TiO₂, and the E_g of the catalyst was narrower. The anatase phase exhibited a higher activity (Pang & Abdullah 2012a). The reactor was not protected from light during the experiments. Thus, the visible light in the laboratory promoted the degradation of toluene in the presence of ion-doped TiO₂. Therefore, the catalytic activity of Ag⁺-doped TiO₂ increased.

The photocatalytic activity increased when TiO₂ was doped by Al³⁺ or Fe³⁺ ions. The ionic radii of Al³⁺ (53.5 pm) and Fe³⁺ (55 pm) are smaller than that of Ti⁴⁺; thus, the ions are easily substituted in the lattice. Two doped ions replace two Ti⁴⁺ ions, and one O²⁻ hole appears. The shape of the crystal changes, which facilitates the generation of the electron-hole pairs. The f_A increased after ion-doping, and the E_g was narrower.

Doping TiO₂ with V⁵⁺, whose valence is higher than that of the parent Ti⁴⁺, results in an increase in the concentration of electrons in the conduction band. An upward shift of the Fermi energy level is also expected. When the dopant concentration increases, the surface barrier becomes higher, and the space charge region becomes narrower. The electron-hole pairs within this region are efficiently separated by the large electric field traversing the barrier before these pairs have the chance to recombine (Kiriakidou *et al.* 1999).

The ionic radii of Cu²⁺, Mn²⁺, Ni²⁺ and Zn²⁺, which are 73, 67, 69, and 74 pm respectively, are slightly larger than that of Ti⁴⁺. The compounding of TiO₂ and doped-metal causes the generation of Ti³⁺. The electrons are transferred to Ti³⁺ and then to the oxygen, which reduces the probability for recombination between electrons and holes. In addition, the holes left in the valence band have more opportunity to participate in the oxidizing reactions because the electrons are effectively scavenged by the doping-ions (Zang *et al.* 1995).

Influence of calcination temperature

Fe³⁺-doped TiO₂ nanotubes containing 1.0% of Fe³⁺ calcined at 450, 500, 550 and 600 °C were prepared to investigate the effect of the calcination temperature. The E_g of the abovementioned catalysts were 3.16, 3.12, 3.06,

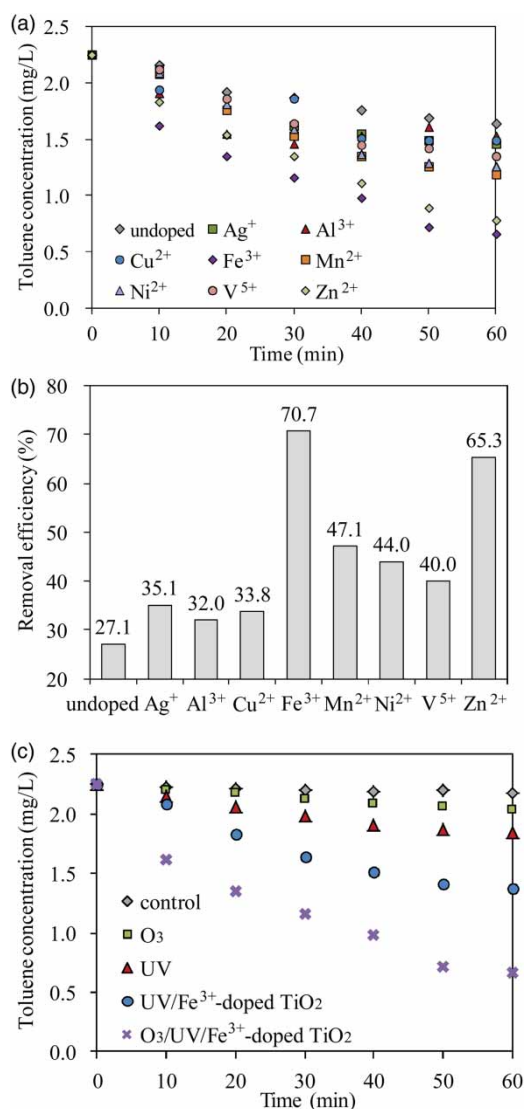


Figure 2 | Removal of toluene for different TiO₂ nanotubes under 254 nm UV irradiation for 60 min. (a) Degradation of 2.25 mg/L toluene versus irradiation time; (b) removal efficiency of toluene for different catalysts; (c) degradation of toluene by O₃, UV, UV/Fe³⁺-doped TiO₂ and O₃/UV/Fe³⁺-doped TiO₂ processes.

and 2.75 eV, whereas the S_{BET} were 122, 120, 118, and 111 m²/g, respectively. The toluene removal efficiencies for the abovementioned catalysts were 40.1%, 62.3, 70.7, and 35.6%, respectively. When the calcination temperature increases, the E_{g} and S_{BET} decrease; the f_{A} increases at first, and then decreases. The E_{g} was broadened although the S_{BET} of TiO₂ nanotubes calcined at 450 and 500 °C are larger. This result lowered the photocatalytic activity. For the 600 °C calcined catalyst, the f_{A} and S_{BET} decreased; thus, the overall efficiency is low. TiO₂ nanotubes calcined at 550 °C had preferred crystallinity, S_{BET} , and E_{g} , which resulted in a higher catalytic activity.

Influence of doping concentration





Fe³⁺-doped TiO₂ nanotubes with Fe³⁺ doping concentration of 0.1, 0.5, 1.0, and 5.0% calcined at 550 °C were prepared. The f_{A} of the abovementioned catalysts were 89.1, 90.3, 87.5, and 87.3%, whereas the E_{g} were 3.10, 3.08, 3.06, and 3.05 eV, and S_{BET} were 170, 141, 118, and 89 m²/g, respectively. The toluene removal efficiencies for the abovementioned catalysts were 47.8, 61.1, 70.7, and 27.3%, respectively. The f_{A} of Fe³⁺-doped TiO₂ increases at first, and then decreases because when TiO₂ is doped by Fe³⁺ ions, the formation of anatase from the amorphous phase is promoted. However, rutile phase formation is significantly promoted when the Fe³⁺ doping concentrations increased. The decline in the phase-transformation temperature can be explained in two ways. First, is that the surface defect density of the TiO₂ nanotubes increases when TiO₂ is doped with Fe³⁺. These defects act as rutile nucleation sites. Second, is that the surface oxygen vacancy concentration of the anatase grains increases in the ion-doped TiO₂ nanotubes and favors the rearrangement of ions as well as the reorganization of the structure to form the rutile phase (Li *et al.* 2011). The highest photocatalytic activity was achieved in the presence of 1.0% Fe³⁺-doped TiO₂ under the effects of all the aforementioned factors.

Mechanism of O₃/UV/Fe³⁺-doped TiO₂ progress

The efficiencies of O₃, UV, UV/Fe³⁺-doped TiO₂ and O₃/UV/Fe³⁺-doped TiO₂ processes for toluene decomposition were also determined. The removal efficiencies for the abovementioned processes were 9.3%, 17.8%, 38.7% and 70.7%, respectively, whereas 3.1% of the toluene volatilized (Figure 2(c)). Compared with other processes, ozonation has a lower toluene decomposition rate because of the lower oxidizability of O₃ compared with that of the •OH generated by the AOP process. The removal efficiency of the UV/Fe³⁺-doped TiO₂ process was lower than that of the O₃/UV/Fe³⁺-doped TiO₂ process, indicating that toluene removal in the UV/Fe³⁺-doped TiO₂ process can be enhanced by ozonation (Yuan *et al.* 2013).

UV and Fe³⁺-doped TiO₂ can enhance the production of •OH through ozonation progress (Equations (4) and (5)) (Wei *et al.* 2011). A valence band electron could be promoted to the conduction band, thereby leaving holes at the valence band (Equation (6)). Fe³⁺ in TiO₂ acts as

a shallow trapping site for charge carriers shown in Equations (7) and (8) (Pang & Abdullah 2012b). The unstable Fe²⁺ and Fe⁴⁺ react with H₂O₂ and OH⁻, and they transfer to Fe³⁺ as shown in reactions (9) and (10) (Wei et al. 2011).



The generated $\cdot\text{OH}$ is a powerful oxidizing agent that can attack toluene. Therefore, toluene was efficaciously removed from the water.

CONCLUSIONS

Ion-doped TiO₂ nanotubes were prepared using Degussa P-25 TiO₂ powders. The ions were effectively incorporated into the TiO₂ lattice, except for Ag⁺. When TiO₂ is doped by ions, the S_{BET} decreases, and the E_g becomes narrower. The photocatalytic activities of catalysts increased when Ag⁺, Al³⁺, Cu²⁺, Fe³⁺, Mn²⁺, Ni²⁺, V⁵⁺, and Zn²⁺ were doped into the TiO₂ nanotubes. Moreover, the 1.0% Fe³⁺-doped TiO₂ nanotubes calcined at 550 °C had the highest catalytic activity because of the effects of the f_A, S_{BET}, E_g, and ion-doping. The toluene removal in the UV/Fe³⁺-doped TiO₂ process can be enhanced by ozonation. The mechanism of O₃/UV/Fe³⁺-doped TiO₂ progress was that the generated $\cdot\text{OH}$ could attack toluene at the surface of TiO₂ or near it.

ACKNOWLEDGEMENT

We gratefully acknowledge the financial support from the National Natural Science Foundation of China (51178043).

REFERENCES

- Adewuyi, Y. G. 2001 *Sonochemistry: environmental science and engineering applications*. *Ind. Eng. Chem. Res.* **40** (22), 4681–4715.
- Carp, O., Huisman, C. L. & Reller, A. 2004 *Photoinduced reactivity of titanium dioxide*. *Prog. Solid State Ch.* **32** (1–2), 33–177.
- Epifani, M., Giannini, C., Tapfer, L. & Vasaneli, L. 2000 *Sol-gel synthesis and characterization of Ag and Au nanoparticles in SiO₂, TiO₂, and ZrO₂ thin films*. *J. Am. Ceram. Soc.* **83** (10), 2385–2393.
- Kiriakidou, F., Kondarides, D. I. & Verykios, X. E. 1999 *The effect of operational parameters and TiO₂-doping on the photocatalytic degradation of azo-dyes*. *Catalysis Today* **54** (1), 119–130.
- Leinen, D., Lassaletta, G., Fernandez, A., Caballero, A., Gonzalez-Elipe, A. R., Martin, J. M. & Vacher, B. 1996 *Ion beam induced chemical vapor deposition procedure for the preparation of oxide thin films. II. Preparation and characterization of Al_xTi_{1-x}O₂ thin films*. *J. Vacuum Sci. Technol. A* **14** (5), 2842–2848.
- Li, X., Zou, X., Qu, Z., Zhao, Q. & Wang, L. 2011 *Photocatalytic degradation of gaseous toluene over Ag-doping TiO₂ nanotube powder prepared by anodization coupled with impregnation method*. *Chemosphere* **83** (5), 674–679.
- Lin, C. & Lin, K. S. 2007 *Photocatalytic oxidation of toxic organohalides with TiO₂/UV: The effects of humic substances and organic mixtures*. *Chemosphere* **66** (10), 1872–1877.
- Pang, Y. L. & Abdullah, A. Z. 2012a *Comparative study on the process behavior and reaction kinetics in sonocatalytic degradation of organic dyes by powder and nanotubes TiO₂*. *Ultrason. Sonochem.* **19** (3), 642–651.
- Pang, Y. L. & Abdullah, A. Z. 2012b *Effect of low Fe³⁺ doping on characteristics, sonocatalytic activity and reusability of TiO₂ nanotubes catalysts for removal of Rhodamine B from water*. *J. Hazard. Mater.* **235–236**, 326–335.
- Ravichandran, L., Selvam, K., Krishnakumar, B. & Swaminathan, M. 2009 *Photovalorisation of pentafluorobenzoic acid with platinum doped TiO₂*. *J. Hazard. Mater.* **167** (1–3), 763–769.
- Spurr, R. A. & Myers, H. 1957 *Quantitative analysis of anatase-rutile mixtures with an X-ray diffractometer*. *Analyt. Chem.* **29** (5), 760–762.
- Sun, L., Li, J., Wang, C. L., Li, S. F., Chen, H. B. & Lin, C. J. 2009 *An electrochemical strategy of doping Fe³⁺ into TiO₂ nanotube array films for enhancement in photocatalytic activity*. *Sol. Energy Mater. Sol. Cells* **93** (10), 1875–1880.
- Takeuchi, M., Hidaka, M. & Anpo, M. 2012 *Efficient removal of toluene and benzene in gas phase by the TiO₂/Y-zeolite hybrid photocatalyst*. *J. Hazard. Mater.* **237–238**, 133–139.

- Wang, W., Varghese, O. K., Paulose, M. & Grimes, C. A. 2004 A study on the growth and structure of titania nanotubes. *J. Mater. Res.* **9** (2), 417–422.
- Wei, M. C., Wang, K. S., Hsiao, T. E., Lin, I. C., Wu, H. J., Wu, Y. L., Liu, P. H. & Chang, S. H. 2011 Effects of UV irradiation on humic acid removal by ozonation, Fenton and Fe₀/air treatment: THMFP and biotoxicity evaluation. *J. Hazard. Mater.* **195**, 324–331.
- Yu, J., Xiang, Q. & Zhou, M. 2009 Preparation, characterization and visible-light-driven photocatalytic activity of Fe-doped titania nanorods and first-principles study for electronic structures. *Appl. Catal. B: Environ.* **90** (3–4), 595–602.
- Yuan, R., Zhou, B., Hua, D. & Shi, C. 2013 Enhanced photocatalytic degradation of humic acids using Al and Fe co-doped TiO₂ nanotubes under UV/ozonation for drinking water purification. *J. Hazard. Mater.* **262**, 527–538.
- Zang, L., Liu, C. Y. & Ren, X. M. 1995 Photochemistry of semiconductor particles: Part 4. – Effects of surface condition on the photodegradation of 2,4-dichlorophenol catalysed by TiO₂ suspensions. *J. Chem. Soc. Faraday Trans.* **91** (5), 917–923.
- Zhang, G. W., He, G. H., Xue, W. L., Xu, X. F., Liu, D. N. & Xu, Y. H. 2012 Enhanced photocatalytic performance of titania nanotubes modified with sulfuric acid. *J. Mole. Catal. A: Chem.* **363–364**, 423–429.
- Zwilling, V., Darque-Ceretti, E., Boutry-Forveille, A., David, D., Perrin, M. Y. & Aucouturier, M. 1999 Structure and physicochemistry of anodic oxide films on titanium and TA6 V alloy. *Surf. Interface Analysis* **27** (7), 629–637.

First received 30 September 2013; accepted in revised form 28 January 2014. Available online 13 February 2014