

# Role of the functional groups in the adsorption of bisphenol A onto activated carbon: thermal modification and mechanism

Guifang Liu, Xuchun Li and Luiza C. Campos

## ABSTRACT

Surface properties of activated carbons play vital roles in adsorption of contaminants. Aiming to improve the adsorption of phenolic endocrine disrupting chemicals (EDCs), commercially activated carbon (W20) was modified via thermal treatment to obtain a carbon sample (W20N) with different characteristics. The content of acidic oxygen-containing groups of W20 was obviously reduced by the thermal modification. Bisphenol A (BPA) was chosen as the target compound. The adsorption results indicated that the acidic oxygen-containing groups (especially carboxyl groups) on the surface of activated carbons weakened the ability of carbon acting as  $\pi$ -donors that lead to the reduction of BPA adsorption. Compared to W20, W20N with a greater number of phenyl groups exhibited higher adsorption capacity for BPA in a wide range of pH (4.0–10.0). Therefore, thermal modification improved BPA adsorption onto activated carbon. Furthermore, thermodynamic analysis and effect of solution pH revealed that BPA adsorption onto W20 and W20N probably followed face-to-face  $\pi$ - $\pi$  dispersion interactions. Coexisting tannic acid (TA) formed BPA-TA complexes and played a negative role in BPA adsorption onto carbon based on the  $\pi$ - $\pi$  dispersion interaction. This study should help broaden the scope of modification methods and the application of activated carbons to enhance the removal of phenolic EDCs.

**Key words** | activated carbon modification, adsorption, bisphenol A, functional groups, tannic acid

**Guifang Liu** (corresponding author)  
College of Aerospace and Civil Engineering,  
Harbin Engineering University,  
Harbin 150001,  
China  
E-mail: liuguifang@126.com

**Xuchun Li**  
School of Environmental Science and Engineering,  
Zhejiang Gongshang University,  
Hangzhou 310018,  
China

**Luiza C. Campos**  
Department of Civil, Engineering and Geomatic  
Engineering,  
University College London (UCL),  
London WC1E 6BT,  
UK

## INTRODUCTION

Phenolic endocrine disrupting chemicals (EDCs) can mimic the biological activity of natural hormones and interfere with the reproductive systems of wildlife and humans. Such chemicals have been frequently detected in aquatic environment (Bolong *et al.* 2010). Thus, the issue of phenolic EDCs in aquatic environments has been of great concern in recent years (Zheng *et al.* 2015).

Many approaches have been attempted to remove phenolic EDCs from water. The adsorption by activated carbon is generally considered to be an efficient method to control organic contaminants. Accordingly, some studies on activated carbon adsorption of phenolic EDCs have been explored. These researches are mainly focused on

adsorption efficiency (Laatikainen *et al.* 2014), solution chemistry, and properties of activated carbons (Bautista-Toledo *et al.* 2005). It is widely recognized that the properties of activated carbons, especially the surface acidic oxygen-containing groups, play significant roles in the adsorbability and adsorption mechanism of aromatic compounds (Vidal *et al.* 2015). On the one hand, acidic oxygen-containing groups can decrease the adsorption of phenolic compounds arising from the  $\pi$ - $\pi$  dispersion interaction between the aromatic ring electrons of the adsorbate and the basal plane electrons on activated carbon (Mahajan *et al.* 1980). On the other hand, these groups may be advantageous to the adsorption of phenolic compounds by

hydrogen bonding interactions between hydroxyl groups of the target compounds and acidic oxygen-containing groups on activated carbon (Jung *et al.* 2013). The complex role of functional groups on the surface of activated carbon in adsorption and mechanism processes indicates the specificity for certain type of pollutants, and thus the modification carried out on activated carbon should depend upon the properties of target compounds accordingly.

Thermal treatment (Menéndez *et al.* 1996) and oxidation modification (Lu *et al.* 2012) are two effective ways to modify the surface functional groups on the surface of activated carbon. Jung *et al.* (2013) found that thermally treated biochars with more acidic oxygen-containing groups showed higher adsorption capacity for phenolic EDCs (bisphenol A (BPA) and 17- $\alpha$ -ethinylestradiol (EE2)) compared to thermal oxidation modified biochars and high performance granular activated carbon (GAC). Furthermore, the adsorption activity might be attributed to H-bonding interaction and  $\pi$ -H-bonding interaction from acidic oxygen-containing groups (H-bonding acceptor) on the adsorbent. Sun *et al.* (2011) also reported that hydrothermal oxidation biochars with diverse oxygen-containing functional groups represented higher adsorption capacity of phenolic EDCs (BPA and EE2) compared to thermally treated biochars with low H/C and O/C ratios. The research of Bautista-Toledo *et al.* (2005), nevertheless, revealed the adsorption of BPA onto activated carbons was mainly based on  $\pi$ - $\pi$  dispersion interaction, and the content of acidic oxygen-containing groups was possibly not the key to controlling the adsorption process. In addition, it was reported that the more acidic oxygen-containing groups originated from nitric acid oxidation of activated carbon was unfavorable for the adsorption of BPA (Liu *et al.* 2009). Obviously, the specific effect of acidic oxygen-containing groups on the removal of phenolic EDCs remains ambiguous due to limited research in this area. Therefore, the in-depth mechanism, based on the change of surface functional groups of activated carbon, still needs to be further explored, which may explain the adsorption of phenolic EDCs onto activated carbon.

It is well known that adsorption onto activated carbon (especially GAC) has obvious advantages as it has high efficiency, easy operation, and no by-products. Currently,

activated carbon has been well applied in removal of pollutants in water, such as halogenated nitrogenous disinfection by-products (Chu *et al.* 2012), natural organic matter (NOM) (Treguer *et al.* 2010), taste and odor (Qasim *et al.* 2000), bacteria (Qasim *et al.* 2000), and so on, during drinking water advanced treatment processes and point-of-use filter systems. However, a major problem of the application is that activated carbon exhibits poor selectivity for some toxic contaminants (Bautista-Toledo *et al.* 2005). To the best of our knowledge, few studies have reported improvement from activated carbon adsorption applied in pollution remediation of phenolic EDCs.

The objectives of this study were to use BPA as a representative of phenolic EDCs to investigate: (i) the effect of thermal modification on the surface properties of activated carbon; (ii) the absorption characteristics of BPA onto two activated carbons with different surface properties (a pristine carbon sample and a modified carbon sample); (iii) the effects of temperature, solution pH, and competition of TA on the adsorption of BPA onto the two activated carbons; and (iv) the adsorption mechanism.


## MATERIALS AND METHODS

### Materials

BPA (99 + % purity) and tannic acid (TA) were purchased from Sigma-Aldrich. In view of the high value of  $\log K_{OW}$  (3.32), the stock solution of BPA was prepared with methanol, which is adsorbed slightly onto activated carbon in water (Giusti *et al.* 1974). The working solution of BPA was obtained by diluting the stock solution with pure water. Other reagents were of analytical grades. The characteristic parameters of BPA are shown in Table 1.

A commercial wood-based GAC WV A1100 (Westvaco, Corp., New York) was used and denoted as W20. The particle size of W20 was 0.4–0.8 mm. The pristine carbon sample was washed using deionized water to an invariable solution pH value and desiccated at 378 K for 24 h. About 9 g of sample W20 was placed in a fused silica tubular reactor. Thermal treatment was carried out for 3 h under  $N_2$  flow ( $100 \text{ mL min}^{-1}$ ) at 873 K, and the modified sample was obtained and termed as W20N.

**Table 1** | Characteristic parameters of BPA

Molecular structure	
Molecular size/nm	Width: 0.94, depth: 0.53, thickness: 0.43 (Bautista-Toledo <i>et al.</i> 2005)
Molecular weight/ g·mol <sup>-1</sup>	228.29
Acid dissociation constant (pKa)	9.6–10.2
Water solubility/mg·L <sup>-1</sup>	120
Octanol/water partition coefficient (logK <sub>OW</sub> )	3.32

More details about material and treatment can be found in our previous study (Liu *et al.* 2009). W20 or W20N (0.01 g) was placed in a series of conical flasks containing 100 mL of TA solution (90 mg L<sup>-1</sup>) with an ionic concentration of 0.1 M (NaCl). The flasks were shaken continuously on an orbital shaker (150 rpm) in a thermostatic chamber at 298 K. After 5 days, the modified activated carbons were filtrated and washed with deionized water to remove free TA, and then dried at 378 K for 24 h. Finally, they were designated as W20-TA and W20N-TA, respectively.

### Characterization of activated carbons

Textural characterization for the carbon samples was determined by N<sub>2</sub> adsorption at 77 K with an Autosorb-1-C automatic adsorption apparatus (Quantachrome, USA). Brunauer–Emmett–Teller equation and density functional theory were applied to analyze the data. The pH of point of zero charge (pH<sub>pzc</sub>) of activated carbon was determined by using the method of Noh & Schwarz (1989). The surface functional groups and basic sites were established by Boehm titrations (Boehm 1966). The elemental content of C, N, and O onto the carbon samples was analyzed with a PHI5700 electron spectroscope for chemical analysis.

### Adsorption experiments

For the isotherm studies, carbon samples (0.01 g) were placed in 250 mL conical flasks containing 100 mL of

BPA solution (20–90 mg L<sup>-1</sup>) containing 1 mM phosphate buffer solution (pH 7.0). The flasks were shaken continuously on an orbital shaker (150 rpm) in a thermostatic chamber at 298 K. Equilibrium was reached after 4 days. Keeping the initial conditions, the effects of temperature, solution pH, and TA on the adsorption of BPA were investigated. The pH of the solution was adjusted using 1.0 mM phosphate buffer solution (pH 3.0–8.0) or 1.0 mM borate buffer solution (pH 9.0–11.0). The effect of TA was conducted through competitive adsorption between BPA and TA from aqueous solutions containing 60 mg L<sup>-1</sup> of BPA and variable TA concentrations (0–60 mg L<sup>-1</sup>). The study was carried out at 298 K, pH 7.0 by using 1 mM phosphate buffer solution at a NaCl concentration of 0.1 M. Furthermore, to analyze the competitive adsorption effect of TA, the maximum adsorption capacities of BPA onto the two tested carbon samples and the preloaded-TA carbon samples (W20-TA and W20N-TA) were also investigated using the aforementioned system with a constant ionic concentration of 0.1 M (NaCl).

The BPA uptake  $Q_{ads}$  (mg g<sup>-1</sup>) was calculated from Equation (1):

$$Q_{ads} = \frac{(C_i - C_e) \cdot V}{m} \quad (1)$$

Here,  $V$  is the solution volume (mL),  $C_i$  is the initial BPA concentration (mg L<sup>-1</sup>),  $C_e$  is the equilibrium BPA concentration (mg L<sup>-1</sup>), and  $m$  is the weight of the dry activated carbon (mg).

### Analytical method

The concentrations of BPA in filtrate separated by filtration using a 0.7 μm fiberglass membrane (GF/F, Whatman) were analyzed by high-performance liquid chromatography (Waters 1525) equipped with a dual wavelength ultraviolet detector (Waters 2487), and determined at 280 nm. A Waters Symmetry<sup>®</sup>C<sub>18</sub> column (4.6 μm × 15 cm, 5 μm) was used to separate BPA where the mobile phase was methanol/water (70:30,  $v/v$ ) at a constant flow rate of 1 mL/min. The TA concentration was measured in a Multi N/C 3100 analyzer (Analytik Jena AG, Germany).

## RESULTS AND DISCUSSION

### Characterization of activated carbons

The N<sub>2</sub> adsorption–desorption isotherms and the pore size distributions of the tested activated carbons are shown in Figures 1 and 2, respectively. The inset (Figure 2) shows the pore size distributions ranging from 10 to 120 nm for the tested activated carbons. The specific textural properties of the activated carbons are reported in Table 2. The N<sub>2</sub> isotherms and the pore size distributions of the W20 and W20N indicate that the textural characteristics of W20 were not drastically changed by thermal treatment, agreeing

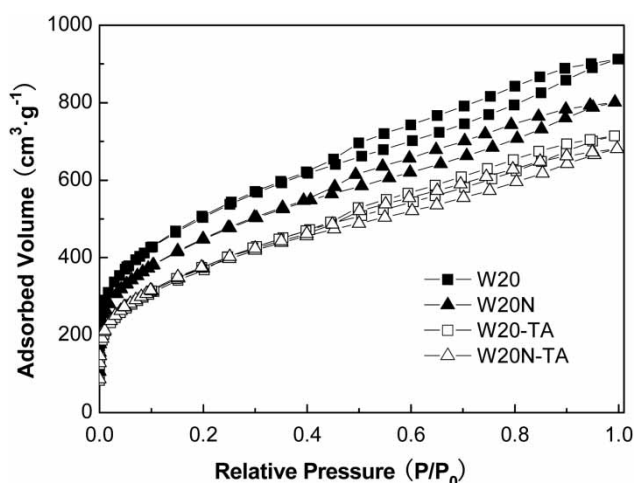


Figure 1 | Adsorption and desorption isotherms of N<sub>2</sub> onto activated carbons.

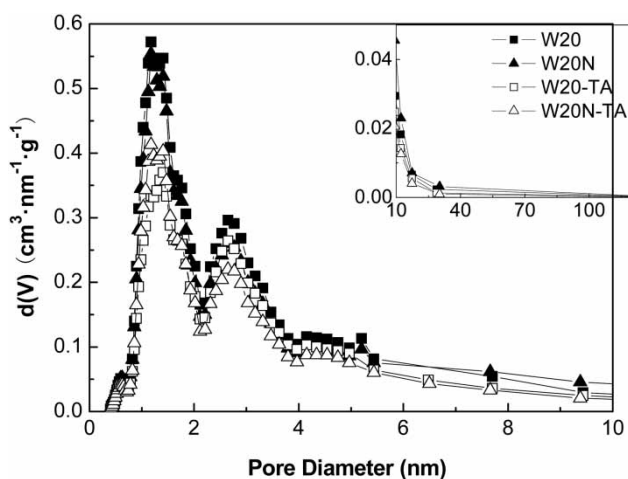


Figure 2 | Pore size distributions of activated carbons.

with previous reports (Menéndez *et al.* 1996). The slight reduction of specific area and total pore volume of W20N might result from the collapse of some of the pore walls during thermal treatment. Table 2 indicates that the average pore diameter (APD) value of W20 was increased from 3.579 to 3.756 nm by thermal treatment. In addition, Figure 2 shows that W20 and W20N were composed of micropores and mesopores. The chemical characteristics of the W20 and W20N, including the oxygen-containing groups, the pH of point of zero charge (i.e., pH<sub>PZC</sub>), and the elemental analysis are given in Table 3. These characterization results indicate that thermal treatment caused the decomposition of some of the acidic oxygen-containing groups (especially for carboxyl groups), which made the density of delocalized  $\pi$  electrons on the oxygen-free Lewis basic sites rise (Menéndez *et al.* 1996). As a result, the basicity of activated carbon was increased, and the pH<sub>PZC</sub> value of W20 was changed from 4.95 to 6.87 after thermal treatment.

### Adsorption isotherm

The adsorption isotherms of BPA onto W20 and W20N are shown in Figure 3. The Langmuir and Freundlich models were employed to analyze experimental data, with the models shown in Equations (2) and (3), respectively.

$$q_e = \frac{q_m K_L C_e}{1 + K_L C_e} \quad (2)$$

$$q_e = K_F C_e^{1/n} \quad (3)$$

Here,  $q_e$  is the BPA uptake per unit mass of activated carbon at equilibrium ( $\text{mg}\cdot\text{g}^{-1}$ );  $C_e$  is the equilibrium concentration of BPA in the bulk of solution ( $\text{mg}\cdot\text{L}^{-1}$ );  $q_m$  is the adsorption capacity corresponding to the complete monolayer coverage of adsorption sites ( $\text{mg}\cdot\text{g}^{-1}$ );  $K_L$  is the constant related to the free energy of adsorption ( $\text{L}\cdot\text{mg}^{-1}$ ).  $K_F$  and  $n$  are the constants related to sorption capacity and sorption intensity of the adsorbent.

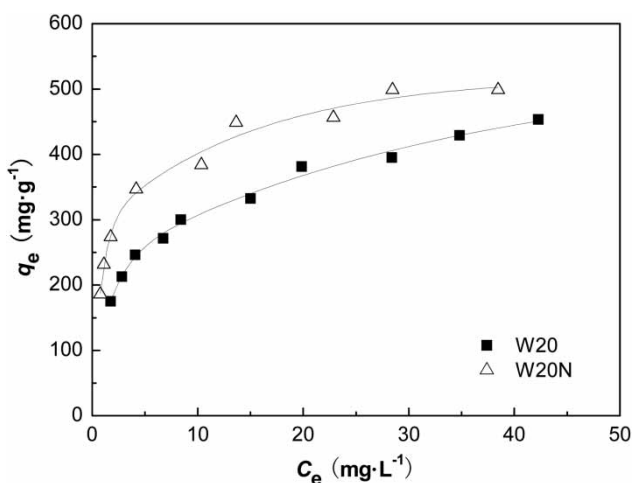
The equilibrium isotherm constants of the above two models are shown in Table 4. The experimental data fitted to the Langmuir model better than to the Freundlich model, according to the higher value of  $R^2$  obtained. Hence, this indicates the presence of a single-layer

**Table 2** | Textural properties of activated carbons

Sample	$S_{\text{BET}}$ ( $\text{m}^2 \text{g}^{-1}$ )	APD (nm)	TPV ( $\text{cm}^3 \text{g}^{-1}$ )	Pore volume distribution ( $\text{cm}^3 \text{g}^{-1}$ )		
				Micropore $d < 2 \text{ nm}$	Mesopore $2 \text{ nm} \leq d \leq 50 \text{ nm}$	Macropore $d > 50 \text{ nm}$
W20	1,767	3.579	1.581	0.486	1.087	0.008
W20N	1,669	3.756	1.567	0.456	1.103	0.008
W20-TA	1,346	3.412	1.148	0.329	0.813	0.006
W20N-TA	1,315	3.227	1.061	0.358	0.699	0.004

**Table 3** | Chemical characteristics of activated carbons

Sample	Hydroxyl group ( $\text{mmol g}^{-1}$ )	Lactone group ( $\text{mmol g}^{-1}$ )	Carboxyl group ( $\text{mmol g}^{-1}$ )	Basic sites ( $\text{mmol g}^{-1}$ )	$\text{pH}_{\text{PZC}}$	C (%)	O (%)	N (%)
W20	0.07	0.27	0.28	0.32	4.95	90.39	9.61	0
W20N	0.08	0.11	0.00	0.45	6.87	95.14	4.86	0

**Figure 3** | Adsorption isotherms of BPA onto activated carbons at 298 K and pH 7.0.**Table 4** | Equilibrium isotherm constants of BPA adsorption onto activated carbons

Sample	Langmuir model constants			Freundlich model constants		
	$q_m$ ( $\text{mg g}^{-1}$ )	$K_L$ ( $\text{L mg}^{-1}$ )	$R^2$	$K_F$	$1/n$	$R^2$
W20	476.19	0.219	0.9916	157.67	0.284	0.9811
W20N	526.32	0.500	0.9961	223.77	0.239	0.9595

adsorption process, where the BPA interacted with the activated carbon surface throughout the adsorption process. Both W20 and W20N represented a high adsorption

capacity to BPA. Especially, the adsorption capacity of W20N reached  $526.32 \text{ mg g}^{-1}$ , which was higher than that of W20. The Langmuir constant  $K_L$  also indicated that W20N had a higher adsorption affinity to BPA than W20.

The thermal modification of activated carbon improved the adsorption capacity of BPA. Considering the slight change of structural properties between W20 and W20N, this may be due to the change of chemical properties on the surface of activated carbon before and after the thermal modification. Usually, the acidic oxygen-containing groups on activated carbons can adsorb more water molecules from solution to form water molecule clusters, which can prevent target organics from accessing the hydrophobic regions of the activated carbon surface. Thus, the more acidic oxygen-containing groups, especially carboxyl groups, on W20 (Table 3) could directly decrease the adsorption of BPA. This result is in agreement with other work investigating the effect of carbon surface acidity on the adsorption of some organic pollutants, such as phenol and nitrobenzene (Coughlin & Ezra 1968). Kim *et al.* (2011) also found that the acidic oxygen-containing groups and the organic moieties (phenyl groups) attached to the surface of adsorbents played a critical role in BPA adsorption.

### Effect of temperature on adsorption

The effect of solution temperature on the removal of BPA was investigated in the range of 288 K to 318 K and pH



7.0. The adsorption isotherms are shown in Figure 4. With an increase in temperature, the equilibrium uptake of BPA decreased with both W20 and W20N. The Langmuir model constants are given in Table 5. As the temperature increased from 288 K to 318 K, the adsorption capacities of BPA decreased from 500.25 to 429.74 mg g<sup>-1</sup> for W20 and from 532.47 to 468.76 mg g<sup>-1</sup> for W20N. This indicates that the low temperature is more favorable for the removal of BPA.

The thermodynamic parameters can offer in-depth information on inherent energetic variations that relate to the adsorption. The Gibbs free energy change ( $\Delta G$ ), enthalpy change ( $\Delta H$ ), and entropy change ( $\Delta S$ ) of BPA adsorption were calculated to analyze the thermodynamic behavior. These thermodynamic parameters were obtained from the following equations:

$$\Delta G = -RT \ln K_L \quad (4)$$

$$\ln K_L = \frac{\Delta S}{R} - \frac{\Delta H}{RT} \quad (5)$$

Here,  $K_L$  is the Langmuir constant at  $T$  (L·mmol<sup>-1</sup>);  $R$  is the universal gas law constant (8.314 J mol<sup>-1</sup> K<sup>-1</sup>);  $T$  is the solution temperature (K). The value of  $\Delta H$  and  $\Delta S$  can be directly obtained from the slope and intercept of the van 't Hoff plots of  $\ln K_L$  versus  $1/T$ , with relevant thermodynamic parameters being listed in Table 5.

The negative Gibbs free energy changes indicated that the adsorption processes of BPA onto W20 and W20N were both spontaneous. The absolute values of  $\Delta G$  were decreased with the increasing temperature, which implies that the increasing temperature was detrimental to the adsorption process. The negative enthalpy change implies that the adsorption process was exothermic. Therefore, the amounts of BPA adsorbed were reduced by the increasing temperatures. The range of 40–120 kJ mol<sup>-1</sup> of enthalpy indicates a chemisorption

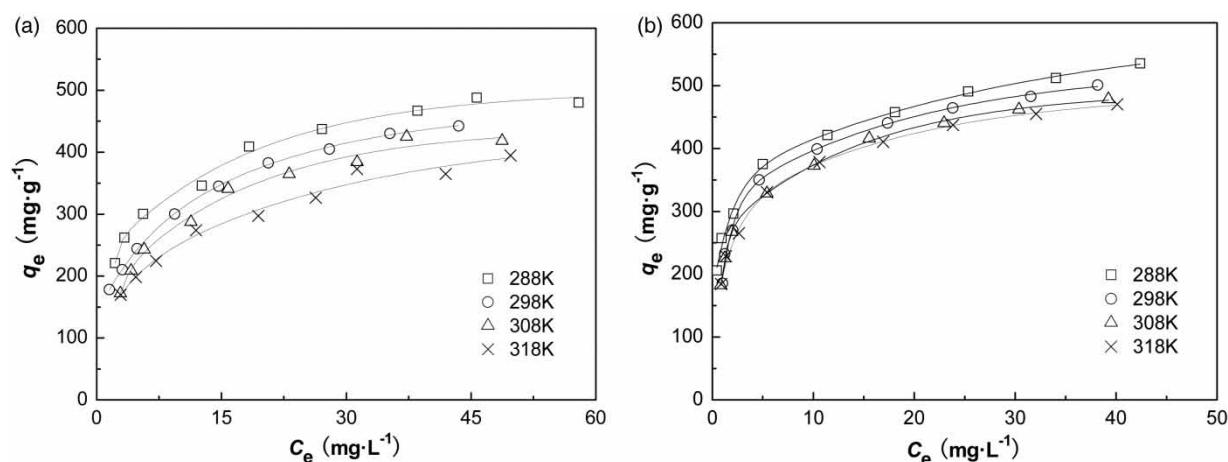


Figure 4 | Adsorption isotherms of BPA at different temperatures onto W20 (a) and W20N (b) at pH 7.0.

Table 5 | Thermodynamic parameters for BPA adsorption onto activated carbons at pH 7.0

T (K)	W20					W20N				
	$q_m$ (mg g <sup>-1</sup> )	$K_L$ (L mmol <sup>-1</sup> )	$\Delta G$ (kJ mol <sup>-1</sup> )	$\Delta H$ (kJ mol <sup>-1</sup> )	$\Delta S$ (kJ mol <sup>-1</sup> )	$q_m$ (mg g <sup>-1</sup> )	$K_L$ (L/mmol)	$\Delta G$ (kJ mol <sup>-1</sup> )	$\Delta H$ (kJ mol <sup>-1</sup> )	$\Delta S$ (kJ mol <sup>-1</sup> )
288	500.25	58.57	-26.29	-12.51	47.93	532.47	141.77	-28.40	-8.55	68.94
298	476.19	50.89	-25.95			526.32	127.16	-28.14		
308	458.30	41.85	-25.48			485.91	111.65	-27.83		
318	429.74	36.14	-25.13			468.76	101.82	-27.61		

mechanism, which is larger than that of physisorption (Hameed 2007). Hence, the enthalpy changes of  $-12.51 \text{ kJ mol}^{-1}$  and  $-8.55 \text{ kJ mol}^{-1}$  in this study mean that the adsorption of BPA onto W20 and W20N is mainly based on physisorption.

Usually, the adsorption of adsorbates is accompanied with the desorption of water molecules, and entropy changes can describe the interaction of the two processes. From Table 5, the entropy change of BPA adsorption onto W20 and W20N was  $47.93 \text{ kJ mol}^{-1}$  and  $68.94 \text{ kJ mol}^{-1}$ , respectively. The entropy change of BPA adsorption onto W20N was larger, which could be attributed to the higher adsorption of BPA onto the modified carbon. To the best of our knowledge, water molecules are liable to form hydrogen bonds with the acidic oxygen-containing groups. Hence, water molecules were more easily released from W20N due to the fewer acidic oxygen-containing groups and the stronger hydrophobicity compared to W20, which promoted BPA adsorption and thus exchanged more water molecules. The entropy changes also indicated the detrimental effect of acidic oxygen-containing groups onto activated carbon samples for BPA adsorption.

### Effect of pH on adsorption

The pH of the solution is a key factor in controlling adsorbate adsorption in the aqueous phase because it determines the charge of both the carbon surface and adsorbate. The adsorption capacity of BPA onto W20 and W20N was investigated in the pH range of 3.0 to 11.0. Figure 5 depicts the variations

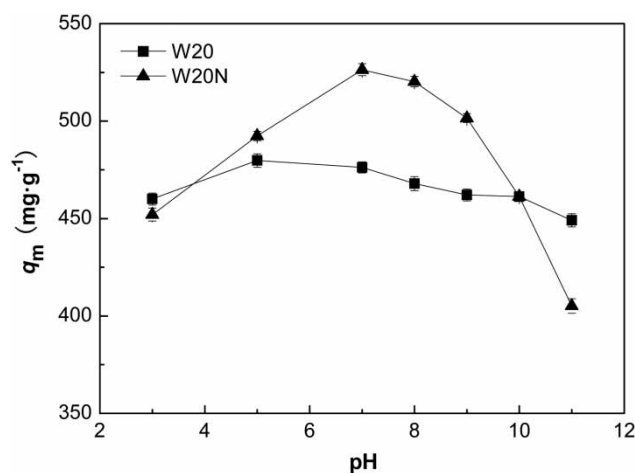


Figure 5 | Effect of solution pH on BPA adsorption onto activated carbons at 298 K.

of saturated adsorption capacities (i.e.,  $q_m$ ) of BPA onto W20 and W20N with respect to the initial pH. Changes in the pH resulted in a minimal adsorption variation of BPA onto W20 (<7%). W20 exhibited the best adsorption capacity ( $479.78 \text{ mg g}^{-1}$ ) at pH 5.0 and the worst ( $449.03 \text{ mg g}^{-1}$ ) at pH 11.0. Compared to W20, W20N represented higher adsorption capacity of BPA in a wide range of pH (4.0–10.0). The adsorption of BPA on W20N increased from pH 3.0 to 7.0 and then dropped from 7.0 to 11.0. The maximal adsorption of  $526.32 \text{ mg g}^{-1}$  onto W20N occurred at pH 7.0 and the poorest adsorption capacity of BPA onto W20N was also observed at pH 11.0. However, the adsorption of BPA onto W20N was also more sensitive to the change in pH due to the obvious change of adsorption with an increase in pH from 3.0 to 11.0.

The results were attributed to the degree of BPA dissociation and the net charge density of activated carbons derived from the surface acidic oxygen-containing groups at different pH values of the solution. The maximum values of BPA adsorption onto W20 and W20N were obtained near the  $\text{pH}_{\text{PZC}}$  of carbon samples (4.95 for W20 and 6.87 for W20N) where BPA is in its molecular state (Bautista-Toledo *et al.* 2005) and the activated carbons represent a surface charge density close to zero. Under these circumstances,  $\pi$ - $\pi$  dispersion interaction and hydrogen bonding interaction could be strengthened. However, as the solution pH value exceeds neutral pH, BPA deprotonates and becomes a negatively charged species (Bautista-Toledo *et al.* 2005). At the same time, considering the  $\text{pH}_{\text{PZC}}$  of W20 (4.95) and W20N (6.87), the surfaces of the W20 and W20N will be negatively charged. Therefore, the electrostatic repulsion, occurring between BPA and the carbon surfaces, weakened the adsorption interaction and reduced the adsorption capacity of BPA. Although the main form of BPA is in the molecular state in the pH range of 3.0 to 7.0, the  $\pi$ - $\pi$  dispersion interaction or hydrogen bonding interaction could also be weakened because of the existence of positive or negative charges on the surface of W20 and W20N (except the  $\text{pH}_{\text{PZC}}$  of activated carbons).

### Effect of TA on adsorption

The naturally occurring NOM has large amounts of phenyl groups and oxygen-containing groups in the molecular structure, which affects the adsorption of organic compounds

onto activated carbon. Here, TA was selected as a model compound for NOM, and its effect on the adsorption of BPA was investigated. The adsorption of BPA with various coexisting concentrations of TA (0–60 mg L<sup>-1</sup>) onto W20 and W20N was carried out at an ionic strength of 0.1 M at pH 7.0. With the adsorption of TA onto W20 and W20N, the surface characteristics of the samples might be changed and thus affect the adsorption of BPA in this competitive system. Thus, the adsorption of BPA onto W20 and W20N preloaded with complete TA coverage (i.e., W20-TA and W20N-TA) was also investigated at an ionic strength of 0.1 M at pH 7.0. In the competitive system, the relative BPA uptake onto W20 and W20N is shown in Figure 6. The  $q_0$  and  $q$  is the amount of BPA adsorption in the absence and presence of TA in the solution, respectively.

As shown in Figure 6, there was no obvious change in the relative BPA uptake ( $q/q_0$ ) at a low concentration of TA (less than 2.5 mg L<sup>-1</sup>). However, as the concentration of TA increased from 2.5 mg L<sup>-1</sup> to 60 mg L<sup>-1</sup>, the  $q/q_0$  values of two activated carbon samples were both decreased and the removal efficiency of BPA was reduced by 16.5% and 19.2% for W20 and W20N at 60 mg L<sup>-1</sup> of TA, respectively. Obviously, the effect of coexisting TA was marked at a higher concentration of TA.

There is likely to be two explanations for this effect. One is that the adsorption of TA onto W20 and W20N possibly leads to the changes of the surface characteristics of the carbon samples and thus decreases the active sites of BPA.

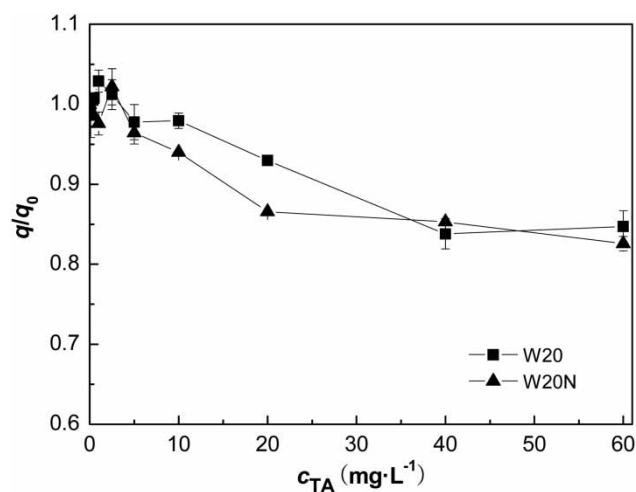


Figure 6 | Relative BPA uptake as a function of the TA concentration.

The other is the formation of BPA-TA complexes. Considering that the surface characteristics change, W20 and W20N loaded with complete TA coverage, W20-TA and W20N-TA, were characterized as shown in Figure 2 and Table 2. It can be seen that the adsorption of TA reduced the specific area and total pore volume of W20 and W20N. The adsorption capacities of BPA onto W20-TA and W20N-TA are given in Table 6. The adsorption capacity of BPA onto W20 and W20N was only reduced by 3.71% and 9.22%, respectively, due to TA coverage. This was mainly attributed to the inaccessibility of TA to most of the micropore structures of the carbon samples due to the steric hindrance effect (Oćwieja *et al.* 2015), and thus BPA adsorption capacities were slightly decreased. This was consistent with a previous study on the effect of NOM preloaded for atrazine adsorption (Hopman *et al.* 1995). Thus, the adsorption of TA could have a little influence on the active sites of BPA onto W20 and W20N. Hence, the formation of BPA-TA complexes might mainly be responsible for the reduction of BPA adsorption in a competitive matrix. Yamamoto *et al.* (2003) reported that TA had a high sorption coefficient for endocrine disruptors with phenolic hydroxyl groups. Zhu *et al.* (2012) also discovered BPA-TA complexes played an important role in reducing the efficiency in adsorptive and extractive removal processes. The molecular size of BPA-TA complexes is much larger than that of BPA, and thus most of the micropores and mesopores of W20 and W20N may be impossible to access by the complexes. Additionally, the dissociation characteristics of BPA-TA complexes differ from BPA and may directly influence the interaction (especially  $\pi$ - $\pi$  dispersion interaction) between BPA and the surface of tested carbon samples. As a result, the formation of BPA-TA complexes obviously reduced the adsorption of BPA onto W20 and W20N in a competitive manner.

Table 6 | Langmuir model constants of BPA adsorption onto activated carbons not preloaded and preloaded with a complete TA monolayer (298 K, pH 7.0, and 0.1 M in NaCl)

Sample	$q_m$ (mg g <sup>-1</sup> )	$K_L$ (L mg <sup>-1</sup> )	$R^2$
W20	500.01	0.220	0.9940
W20-TA	481.46	0.073	0.9957
W20N	529.10	0.388	0.9977
W20N-TA	480.31	0.125	0.9943



## Adsorption mechanism

It is well known that the surface groups of the adsorbent can interact with the organic adsorbate and affect the adsorption of the latter. That means the hydrophilic and hydrophobic groups on the surface of activated carbons may interact with hydroxyl groups and organic moieties of adsorbate, respectively. Similar interactions in the adsorption of alkylphenols and alkylanilines on alkyl-grafted mesoporous alumina and silica were reported by Inumaru *et al.* (2006). Hence, BPA could also have two types of adsorbate–adsorbent interactions with W20 and W20N in this present study. One is of hydrogen-bonding interaction between the hydroxyl groups of BPA and the hydrophilic groups (such as carboxyl groups and hydroxyl groups) of the tested activated carbons. The other is of  $\pi$ - $\pi$  dispersion interactions between the benzene rings of BPA and the phenyl groups of W20 and W20N. Based on the lower acidic oxygen-containing groups (Table 3) and higher BPA adsorption capacity (Table 4) of W20N, the adsorption mechanism of BPA onto activated carbon could be mainly based on  $\pi$ - $\pi$  dispersion interactions. The possible adsorption manner is shown in Figure 7.

The  $\pi$ - $\pi$  dispersion interaction could also be elaborated by the thermodynamic parameters. The value of  $25 \text{ kJ mol}^{-1}$  of  $-\Delta G$  was proposed as the evidence of  $\pi$ - $\pi$  dispersion

interaction that exists between  $\pi$ -acceptor and carbon sample by Zhu & Pignatello (2005). In this study, the values of  $-\Delta G$  (Table 5) are close to  $25 \text{ kJ mol}^{-1}$ , therefore, the adsorption of BPA onto W20 and W20N should be mainly due to the  $\pi$ - $\pi$  dispersion interaction. BPA had two adsorption forms on the activated carbon surface, as depicted in Figure 7. The positive values of  $\Delta S$  in Table 5 suggest that the increase in  $\Delta S$  from the desorption of water molecules was larger than the decrease in  $\Delta S$  from BPA adsorption. It can be speculated that more water molecules were released from activated carbon samples to meet the BPA adsorption. Thus, the BPA molecular adsorption probably followed the face-to-face  $\pi$ - $\pi$  dispersion interaction, which needs more surface area (Figure 7). The parallel  $\pi$ - $\pi$  dispersion interaction also occurred between PAHs and NOM because NOM has similar molecular structures to activated carbon (Zhu *et al.* 2004).

Generally, the acidic oxygen-containing groups on the surface of the activated carbon sample can weaken the ability of the carbon sample acting as  $\pi$ -donors (Keiluweit & Kleber 2009), and thus affect  $\pi$ - $\pi$  dispersion interactions between activated carbon and BPA. The more phenyl groups on activated carbon are released, the better the BPA adsorption (Hu *et al.* 2009). Compared to W20, W20N had a greater number of phenyl groups, which enhanced the  $\pi$ - $\pi$  dispersion interactions and made the BPA adsorption capacity of W20N better and more sensitive than that of W20 at the range of pH 4.0–10.0 (Figure 5). Similar findings on the effects of acidic oxygen-containing groups on the adsorption of 4-nonylphenol (one of the phenolic EDCs) onto multi-walled carbon nanotubes were also reported by Li *et al.* (2011). Furthermore, TA with a structural formula similar to the activated carbon samples was also engaged in  $\pi$ - $\pi$  dispersion interaction with organic compounds carrying aromatic moieties (Keiluweit & Kleber 2009). From Figure 6, the coexisting TA reduced the adsorption of BPA onto the tested carbon samples. Therefore, TA could act as  $\pi$ -donors and compete for BPA with carbon samples as a result of forming BPA–TA complexes and decreasing the adsorption capacities of activated carbons. Considering the effect of BPA–TA complexes and the stronger  $\pi$ - $\pi$  dispersion interaction between BPA and W20N at pH 4.0–10.0, the effect of TA on the adsorption of BPA onto W20N was more serious (Figure 7).

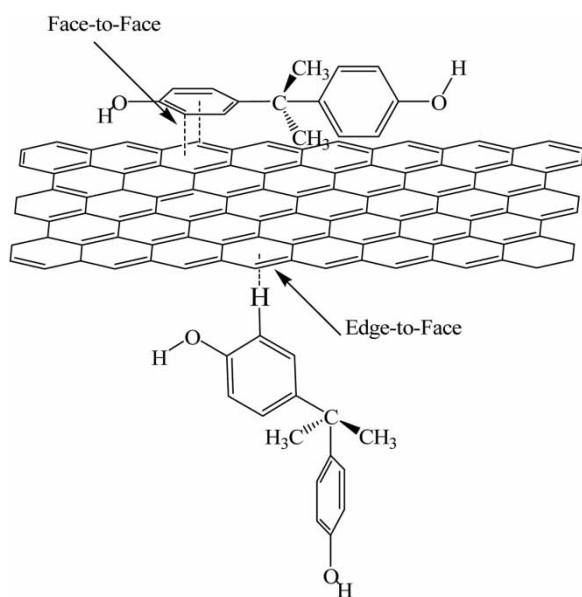


Figure 7 | Arrangement of  $\pi$ - $\pi$  dispersion interaction between BPA and activated carbon.

## CONCLUSIONS

In this work, a commercially activated carbon, W20, was modified by thermal treatment under N<sub>2</sub> flow. Both the pristine and the modified W20 displayed high adsorption capacity for BPA. The Langmuir isotherm model well describes the BPA adsorption onto two tested carbons.

The increase of temperature from 288 K to 318 K impaired the adsorption of BPA onto W20 and W20N. The best adsorption of BPA occurred at pH values close to the isoelectric pH values of the two tested carbon samples with the change of solution pH from 3.0 to 11.0, where the adsorption of BPA onto W20N was more sensitive than that onto W20. TA reduced the adsorption of BPA onto W20 and W20N by acting as a  $\pi$ -donor and forming BPA-TA complexes.

The adsorption mechanism of BPA onto tested carbon samples was mainly due to the  $\pi$ - $\pi$  dispersion interactions. However, the thermal treatment of activated carbon decreased the content of acidic oxygen-containing groups and thus increased the hydrophobic nature of carbon, resulting in the increase in the adsorption capacity of BPA. The results further indicated that the acidic oxygen-containing groups on the surface of the carbon samples were unfavorable for the removal of BPA from aqueous solution. The results are expected to help broaden the scope of activated carbon modification to increase the removal efficiency of phenolic EDCs by activated carbon.

## ACKNOWLEDGEMENTS

This work was supported by the National Natural Science Foundation of China (21307057), the China Scholarship Council (201406685037), the Postdoctoral Science Foundation of Heilongjiang Province (LBH-Z13062), the Natural Science Foundation of Jiangsu Province (BK20130577), and the Specialized Research Fund for the Doctoral Program of Higher Education of China (20130091120014).

## REFERENCES

Bautista-Toledo, I., Ferro-García, M. A., Rivera-Utrilla, J., Moreno-Castilla, C. & Vegas Fernández, F. J. 2005 *Bisphenol A*

- removal from water by activated carbon. Effects of carbon characteristics and solution chemistry. *Environmental Science & Technology* **39** (16), 6246–6250.
- Boehm, H. P. 1966 Chemical identification of surface groups. *Advances in Catalysis* **16**, 179–274.
- Bolong, N., Ismail, A. F., Salim, M. R., Rana, D., Matsuura, T. & Tabe-Mohammadi, A. 2010 Negatively charged polyethersulfone hollow fiber nanofiltration membrane for the removal of bisphenol A from wastewater. *Separation and Purification Technology* **73** (2), 92–99.
- Chu, W., Gao, N., Yin, D., Deng, Y. & Templeton, M. R. 2012 Ozone-biological activated carbon integrated treatment for removal of precursors of halogenated nitrogenous disinfection by-products. *Chemosphere* **86** (11), 1087–1091.
- Coughlin, R. W. & Ezra, F. S. 1968 Role of surface acidity in the adsorption of organic pollutants on the surface of carbon. *Environmental Science & Technology* **2** (4), 291–297.
- Giusti, D. M., Conway, R. A. & Lawson, C. T. 1974 Activated carbon adsorption of petrochemicals. *Journal Water Pollution Control Federation* **46** (5), 947–965.
- Hameed, B. H. 2007 Equilibrium and kinetics studies of 2,4,6-trichlorophenol adsorption onto activated clay. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* **307** (1–3), 45–52.
- Hopman, R., Siegers, W. G. & Kruithof, J. C. 1995 Organic micropollutant removal by activated carbon fiber filtration. *Water Supply* **13** (3–4), 257–261.
- Hu, Q., Li, J. J., Hao, Z. P., Li, L. D. & Qiao, S. Z. 2009 Dynamic adsorption of volatile organic compounds on organofunctionalized SBA-15 materials. *Chemical Engineering Journal* **149** (1–3), 281–288.
- Inumaru, K., Nakano, T. & Yamanaka, S. 2006 Molecular selective adsorption of alkylphenols and alkylanilines from water by alkyl-grafted mesoporous alumina: a comparative study to alkyl-grafted mesoporous silica. *Microporous and Mesoporous Materials* **95** (1–3), 279–285.
- Jung, C., Park, J., Lim, K. H., Park, S., Heo, J., Her, N., Oh, J., Yun, S. & Yoon, Y. 2013 Adsorption of selected endocrine disrupting compounds and pharmaceuticals on activated biochars. *Journal of Hazardous Materials* **263**, 702–710.
- Keiluweit, M. & Kleber, M. 2009 Molecular-level interactions in soils and sediments: the role of aromatic  $\pi$ -systems. *Environmental Science & Technology* **43** (10), 3421–3429.
- Kim, Y., Lee, B., Choo, K. & Choi, S. 2011 Selective adsorption of bisphenol A by organic-inorganic hybrid mesoporous silicas. *Microporous and Mesoporous Materials* **138** (1), 184–190.
- Laatikainen, K., Laatikainen, M., Bryjak, M., Sainio, T. & Siren, H. 2014 Adsorption of bisphenol A from water-ethanol mixtures on pulverized activated carbon. *Separation Science and Technology* **49** (5), 763–772.
- Li, X., Zhao, H., Quan, X., Chen, S., Zhang, Y. & Yu, H. 2011 Adsorption of ionizable organic contaminants on multi-walled carbon nanotubes with different oxygen contents. *Journal of Hazardous Materials* **186** (1), 407–415.

- Liu, G., Ma, J., Li, X. & Qin, Q. 2009 Adsorption of bisphenol A from aqueous solution onto activated carbons with different modification treatments. *Journal of Hazardous Materials* **164** (2–3), 1275–1280.
- Lu, X., Jiang, J., Sun, K., Xie, X. & Hu, Y. 2012 Surface modification, characterization and adsorptive properties of a coconut activated carbon. *Applied Surface Science* **258** (20), 8247–8252.
- Mahajan, O. P., Moreno-Castilla, C. P. L. & Walker, J. R. 1980 Surface-treated activated carbon for removal of phenol from water. *Separation Science and Technology* **15** (10), 1733–1752.
- Menéndez, J. A., Phillips, J., Xia, B. & Radovic, L. R. 1996 On the modification and characterization of chemical surface properties of activated carbon: in the search of carbons with stable basic properties. *Langmuir* **12** (18), 4404–4410.
- Noh, J. S. & Schwarz, J. A. 1989 Estimation of the point zero charge of simple oxides by mass titration. *Journal of Colloid and Interface Science* **130** (1), 157–164.
- Oćwieja, M., Adamczyk, Z. & Morga, M. 2015 Adsorption of tannic acid on polyelectrolyte monolayers determined in situ by streaming potential measurements. *Journal of Colloid and Interface Science* **438**, 249–258.
- Qasim, S. R., Motley, E. M. & Zhu, G. 2000 *Water Works Engineering – Planning, Design & Operating*, 1st edn. Prentice Hall, Upper Saddle River, NJ, USA, pp. 11–36.
- Sun, K., Ro, K., Guo, M., Novak, J., Mashayekhi, H. & Xing, B. 2011 Sorption of bisphenol A, 17 $\alpha$ -ethinyl estradiol and phenanthrene on thermally and hydrothermally produced biochars. *Bioresource Technology* **102** (10), 5757–5763.
- Treguer, R., Tatin, R., Couvert, A., Wolbert, D. & Tazi-Pain, A. 2010 Ozonation effect on natural organic matter adsorption and biodegradation – application to a membrane bioreactor containing activated carbon for drinking water production. *Water Research* **44** (3), 781–788.
- Vidal, C. B., Seredych, M., Rodríguez-Castellón, E., Nascimento, R. F. & Bandosz, T. J. 2015 Effect of nanoporous carbon surface chemistry on the removal of endocrine disruptors from water phase. *Journal of Colloid and Interface Science* **449**, 180–191.
- Yamamoto, H., Liljestrand, H. M., Shimizu, Y. & Morita, M. 2003 Effects of physical-chemical characteristics on the sorption of selected endocrine disruptors by dissolved organic matter surrogates. *Environmental Science & Technology* **37** (12), 2646–2657.
- Zheng, B., Liu, R., Liu, Y., Jin, F. & An, L. 2015 Phenolic endocrine-disrupting chemicals and intersex in wild crucian carp from Hun River, China. *Chemosphere* **120**, 743–749.
- Zhu, D. Q. & Pignatello, J. J. 2005 Characterization of aromatic compound sorptive interactions with black carbon (charcoal) assisted by graphite as a model. *Environmental Science & Technology* **39** (7), 2033–2041.
- Zhu, D., Hyun, S., Pignatello, J. J. & Lee, L. S. 2004 Evidence for  $\pi$ - $\pi$  electron donor-acceptor interactions between  $\pi$ -donor aromatic compounds and  $\pi$ -acceptor sites in soil organic matter through pH effects on sorption. *Environmental Science & Technology* **38** (16), 4361–4368.
- Zhu, F., Choo, K., Chang, H. & Lee, B. 2012 Interaction of bisphenol A with dissolved organic matter in extractive and adsorptive removal processes. *Chemosphere* **87** (8), 857–864.

First received 25 May 2016; accepted in revised form 20 November 2016. Available online 30 January 2017