



The Society shall not be responsible for statements or opinions advanced in papers or discussion at meetings of the Society or of its Divisions or Sections, or printed in its publications. Discussion is printed only if the paper is published in an ASME Journal. Authorization to photocopy material for internal or personal use under circumstance not falling within the fair use provisions of the Copyright Act is granted by ASME to libraries and other users registered with the Copyright Clearance Center (CCC) Transactional Reporting Service provided that the base fee of \$0.30 per page is paid directly to the CCC, 27 Congress Street, Salem MA 01970. Requests for special permission or bulk reproduction should be addressed to the ASME Technical Publishing Department.

Copyright © 1997 by ASME

All Rights Reserved

Printed in U.S.A.

## CORROSION RESISTANT SINGLE CRYSTAL SUPERALLOYS FOR INDUSTRIAL GAS TURBINE APPLICATION

G. L. Erickson

Cannon-Muskegon Corporation  
(a subsidiary of SPS Technologies)  
P.O. Box 506  
Muskegon, MI 49443-0506 U.S.A.



### ABSTRACT

Two different, non-Re containing single crystal (SX) superalloys are defined primarily for industrial turbine application. The alloys, CMSX®-11B and CMSX®-11C, contain respective chromium levels of about 12.5% and 14.5%. Both materials develop unique and extremely good blends of hot corrosion and oxidation resistance. They exhibit extremely good castability, employ relatively simple solution heat treatments and provide creep strength which is as good or better in comparison to other first generation SX materials such as CMSX-2/3, PWA 1480 and René N4. Moreover, at certain engine-pertinent temperature/stress conditions, and particularly in long-term tests (greater than 1,000 hours duration), the alloys appear to exhibit density corrected rupture strengths which are similar or better than CMSX-4® and other second generation SX casting superalloys.

### NOMENCLATURE

ABB = Asea Brown Boveri  
AC = air cool  
ATS = advanced turbine systems  
CAGT = Collaborative Advanced Gas Turbine  
CC = conventional-cast  
CM = Cannon-Muskegon Corporation  
CMSX® = Cannon-Muskegon Corporation Single Crystal  
DOE = Department of Energy  
DS = Directionally solidified, columnar grain  
gm/cm<sup>2</sup> = grams per square centimeter -- density

GW = gigga-watt  
h = hours  
Hrs. = hours  
kg = kilogram  
kg/dm<sup>3</sup> = kilograms per cubic dyne meter -- density  
ksi = thousand pounds per square inch  
LC = low carbon  
LMP = Larson-Miller parameter  
LNG = liquid natural gas  
mm = millimeter  
MPa = mega-pascals  
MW = mega-watt  
Na<sub>2</sub>SO<sub>4</sub> = sodium sulfate  
nm = nanometers  
NO<sub>x</sub> = nitrate  
P = Larson-Miller parameter  
ppm = part per million  
R&D = research and development  
SC = single crystal  
SO<sub>x</sub> = sulfate and/or sulfite  
SX = single crystal  
T = temperature  
t = time  
TCP = topologically close-packed phase  
TET = turbine entry temperature  
°C = ° centigrade  
°F = ° fahrenheit  
μm = microns or micrometers

CM 247 LC®, CM 186 LC®, CMSX-2®, CMSX-3®, CMSX-4®, CMSX-6®, CMSX®-10, CMSX®-11B AND CMSX®-11C are registered trademarks of the Cannon-Muskegon Corporation.

Presented at the International Gas Turbine & Aeroengine Congress & Exhibition  
Orlando, Florida — June 2-June 5, 1997

% = percent  
 $\gamma$  = gamma phase  
 $\gamma'$  = gamma prime phase

**INTRODUCTION**

The land-based, combustion turbine industry is experiencing tremendous growth, in part due to public utility commission rulings and environmental considerations. Prevailing rulings appear inconsistent with the long term, high capital expenditure associated with coal and nuclear power projects, thereby making the utility industry increasingly reliant on combustion turbine technology for its power generation requirements.

Forecast International predicts that 9,958 industrial and marine gas turbine units will be manufactured during the 1994-2003 period. This represents about 7.9% of the total combustion turbine engine market predicted during the period, and is expected to result in an approximate 550 GW electric power capacity expansion being realized throughout the world (Turbomachinery International Handbook, 1994). See Table I.

**Table I**


**Anticipated Electric Power Capacity Additions (GW) Occurring During the Period 1994-2003 (Turbomachinery International Handbook, 1994).**

	FI*	UDI**
Asia/Pacific	245 - 266	249
Europe (inc CIS)	90 - 98	113
North America	95 - 100	94
Central/South America	50 - 58	51
Middle East & Africa	42 - 44	40


\* Forecast International, 1994-2003  
 \*\* Utility Data Institute, 1993-2002

Of the anticipated power capacity increase, a significant portion of the turbines manufactured will utilize fossil fuels (Fig. 1). Additionally, the new industrial and marine gas turbines are expected to range in size as presented in Fig. 2.

Complementary to the Forecast International predictions, the General Electric Company forecasts that base-load electric power generation combustion turbines (CT) and combined cycle (CC) plants will account for about 45% of the new global orders and 66% of the new orders placed in the United States through the year 2001 (Independent Power Report, 1992). Advances in turbine design, materials, cooling technology and coatings have helped develop this market. Current advanced combustion turbines typically achieve more than 35% efficiency in the simple cycle mode and greater than 50% efficiency in the combined cycle mode. For example, Asea Brown Boveri's (ABB's) recent definition of its new gas turbine machine characteristics reveals that a simple cycle efficiency of 37.8% and combined cycle

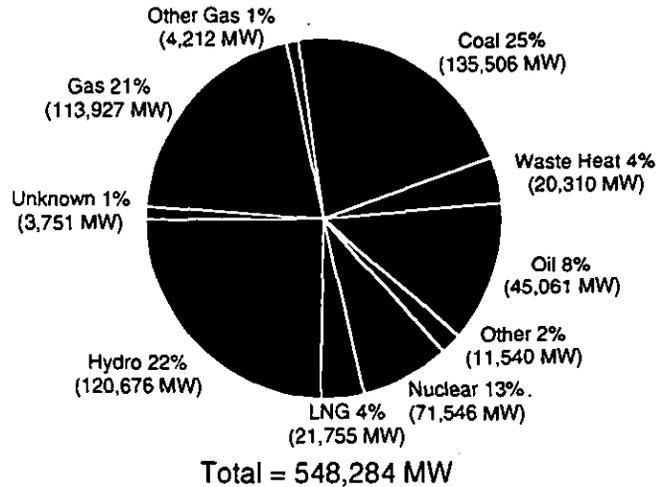

**Figure 1 - Worldwide electric power generating capacity additions predicted for the period 1994-2003. Data presented on the basis of fuel type employed (Turbomachinery International Handbook, 1994).**

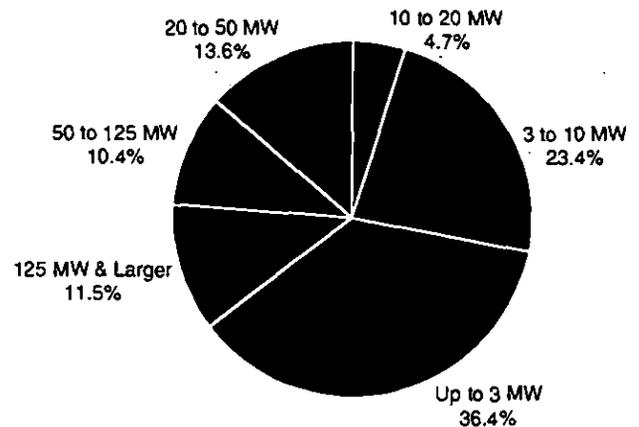

**Figure 2 - Anticipated world gas turbine industry power generation machine market for period 1994-2003. Data presented in terms of production by power class (Turbomachinery International Handbook, 1994).**

efficiency of 58.5% are anticipated for their GT 26 model; this being achieved through increasing power density and mass flow by doubling the pressure ratio (up from 15.0 in the GT 13E2 to 30.0) combined with sequential combustion at a relatively low maximum firing temperature (Turbomachinery International, 1994 a).

And still another industry giant, Siemens, appears to rely on a more moderate increase to engine pressure ratio (eg., 16.0 for the Siemens V84.3 model versus 10.8 in its V84.2 machine) albeit in tandem with increased firing temperature, mass flow,

compressor and turbine efficiencies. It's reported that the V84.3 firing temperature is expected to be 1310°C (2350°F) in contrast to the model V84.2 at 1120°C (2050°F). Furthermore, vane cooling increases from three to four stages while blade cooling is similarly increased from two to three stages (Farmer, 1993). Further design improvements incorporated in the Siemens V84.3A engine are reported to allow an additional increase to firing temperature of about 22°C (40°F) while continuing to maintain acceptable NOx level (Barker, 1995).

In order to achieve these increased firing temperatures which result in thermal efficiency improvement, large industrial turbine designers are beginning to utilize higher technology materials in their respective engine hot sections than previously applied. Where alloys such as IN 738 LC and IN 939 (Table II) were previously employed, the search for greater engine efficiency has led the industrial turbine community to adopt technologies which have already been commercially applied within the aero-turbine and small industrial engine community, eg., directionally solidified columnar grain and single crystal components, serpentine and film cooling designs, as well as certain advanced coatings technology. While Siemens is apparently the first large frame turbine producer to announce the usage of SX components within their new turbines (Farmer, 1995), it is also accepted that most other large turbine producers have designed SX components into their new products.

Complementary to the internal engine company R&D efforts aimed toward improving industrial turbine efficiencies, industry collaborative programs targeted toward developing and commercializing ultra-high efficiency, environmentally superior, cost-competitive gas turbine systems for base-load applications [with a 1427°C (2600 °F) or greater firing temperature] such as

the U.S. Department of Energy (DOE) Advanced Turbine Systems (ATS) Program (World Power Systems Intelligence, 1993) are extremely active. While the ATS Program continues toward its goal of achieving greater than 60% net efficiency for utility scale combined cycles and a 15% jump in efficiency for small industrial machines (Stambler, 1995), similarly aimed activities of the Collaborative Advanced Gas Turbine (CAGT) Program encompassing joint efforts between 17 parties in North America and Europe (Turbomachinery International, 1994 b) further complement the efforts of the European Collaborative Programmes on High Temperature Materials (COST-501 and COST-505) initiated and supported by the Commission of the European Communities, plus the DOE sponsored ATS program.

To similar end, this narrative reports on the development of two single crystal casting alloys exhibiting characteristics which are hoped attractive to the industrial turbine community. Specifically, both alloys provide IN 738 LC - type hot corrosion resistance in tandem with CM 186 LC level oxidation resistance. The alloys' capability to exhibit good hot corrosion resistance concurrent to providing extremely good oxidation resistance is thought unique in the industry, as most alloys exhibit only one or the other. Combined with this positive characteristic, the alloys exhibit extremely good castability ( in small or large components), are able to be solution heat treated in a relatively short period and provide extremely good creep-rupture strength. In certain engine-significant temperature/stress conditions, the alloys exhibit stress-rupture strength, on a density-corrected basis, which is similar to second generation Re-containing alloys such as CMSX-4 and PWA 1484. Furthermore, the alloys appear to exhibit greater long-term rupture strength than CMSX-4 alloy. Moreover, since the alloys do not contain Re, they are at least

**Table II**  
**Nominal Compositions of Selected Alloys.**

	C	Cr	Co	Mo	W	Re	Ta	Cb	Al	Ti	B	Zr	Hf	Ni	Si	Mn	Fe	Y <sub>2</sub> O <sub>3</sub>
IN 738 LC	.010	16.0	8.4	1.7	2.5	-	1.7	0.7	3.6	3.4	.010	.05	-	BASE	-	-	-	-
IN 939	.15	22.5	19.0	-	2.0	-	1.4	1.0	1.9	3.7	.010	.10	-	BASE	-	-	-	-
IN 792	.14	12.7	9.0	2.0	4.2	-	4.2	-	3.4	4.1	.015	.05	1.0	BASE	-	-	-	-
René 80 H	.07	12.9	9.6	4.0	4.9	-	-	-	3.0	4.5	.015	.01	.75	BASE	-	-	-	-
CM 247 LC	.07	8.1	9.2	.5	9.5	-	3.2	-	5.6	0.7	.015	.015	1.4	BASE	-	-	-	-
CM 186 LC	.07	6.0	9.0	.5	8.0	3.0	3.0	-	5.7	0.7	.015	.005	1.4	BASE	-	-	-	-
FSX 414	.25	29	BAL	-	7.5	-	-	-	-	-	.005	-	-	11	.9	.4	.9	-
MA 6000	.05	15	-	2.0	4.0	-	2.0	-	4.5	2.5	.01	.15	-	BASE	-	-	-	1.1
IN 713 C	.10	13.5	-	4.2	-	-	-	2.2	6.1	0.8	.010	.06	-	BASE	-	-	-	-
MARM200Hf	.13	8.3	9.3	-	11.7	-	-	0.9	5.0	1.9	.015	.01	1.8	BASE	-	-	-	-

50% cheaper per pound of alloy purchased, in comparison to 3 wt.% Re-containing alloys, a consequence which could have significant impact on large casting component costs.

### ALLOY DESIGN

Industrial gas turbine engines have historically operated in temperature/pressure regime where Type II hot corrosion attack was the dominating environmental issue (Fig. 3). However, as the industry has sought to improve engine efficiency, engine firing temperatures have generally increased, thereby creating need for materials more able to endure exposures where a blending of Type I hot corrosion and oxidation predominates.

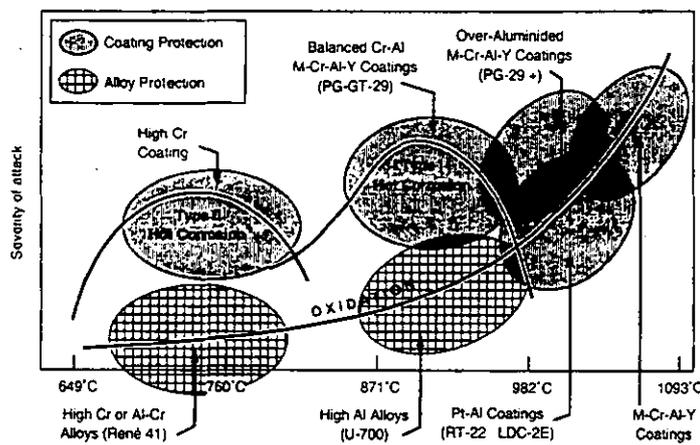


Figure 3 - The Protection Scene (Sims, 1989).

To best achieve the perceived environmental need, moderate alloy chromium levels must be utilized in an alloy's design. As it appears that each turbine producer requires different blends of hot corrosion/oxidation/strength characteristic, two different chromium levels were used as starting points for the CMSX-11B (12.5%) and CMSX-11C (14.5%) alloy designs.

Along with relatively high chromium contributing to alloy environmental properties, other considerations applied to the designs include the selection of low molybdenum level, moderate Ta and elevated Ti: Al ratio. Relatively high Al+Ti levels are employed, which in tandem with moderate alloy Ta level, helps provide the high strength achieved. Furthermore, the alloys' respective designs are thought to result in lower  $\gamma/\gamma'$  lattice misfit parameters than those typically prevailing with second generation SX materials, thereby effecting surprisingly good stress-rupture characteristics in at least the 980-1040°C test regime.

Similarly, the alloy systems employ moderate tungsten levels for solid solution strengthening, however, the alloys also engage Ta: W ratios greater than unity to assist with SX component castability. Partly necessitated by the relatively high chromium levels employed, and the desired levels of W + Ta content, alloy cobalt levels are set relatively low to ensure adequate microstructural stability.

An overview of these alloy design considerations are provided in Fig. 4, while more specific chemistry detail is provided in Table III, where the CMSX-11B and CMSX-11C alloy nominal compositions are compared to other first, second and third generation SX superalloys which have gained some commercial significance, albeit mostly in aero-turbine application. Note that the CMSX-11 derivatives do not rely on Re additions for strength attainment and that the alloys may, therefore, exhibit more desirable long-term lives and utility in certain components due to their inherently lower tendency for phasial instability in the temperature regime where Re containing alloys tend to form Topologically-Close-Packed (TCP) phase.

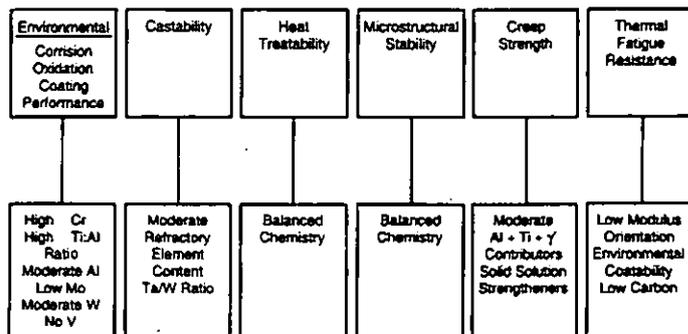


Figure 4 - Alloy design criteria.

The CMSX-11 alloy derivatives are moderate density materials due to their high chromium and Al+Ti levels. The density of CMSX-11B is 8.44 kg/dm<sup>3</sup> while it is 8.36 kg/dm<sup>3</sup> for CMSX-11C; this in comparison to CMSX-3 at 8.56 kg/dm<sup>3</sup>, CMSX-4 at 8.70 kg/dm<sup>3</sup> and CMSX-10 at 9.05 kg/dm<sup>3</sup>.

### ALLOY MANUFACTURE

The CMSX-11B and CMSX-11C alloys are VIM produced according to the process considerations detailed by Erickson (1994). Due to the relatively high alloy chromium contents employed, judicious Cr raw material selection is required to achieve the low levels of residual sulfur and phosphorus desired in the alloy product. Similarly, since low master alloy gas contents are always preferred, and high chromium and titanium containing alloys notoriously exhibit higher residual nitrogen levels, careful raw material selection in tandem with proper VIM procedure development are paramount to quality attainment.

Approximately twenty developmental 136 kg. heats have been produced through the development process. Consistency of major element heat chemistries are easily achieved, and typical tramp element levels prevailing in the CMSX-11 derivatives are illustrated in Table IV. The levels achieved, except for gas content, are typical of those predominating in other SX alloys, such as CMSX-4 and CMSX-10. The abnormally high level of nitrogen in the CMSX-11 derivatives (4 ppm vs. 1 ppm) is a function of alloy chromium content, while the 4 ppm oxygen

**Table III**  
**Nominal Compositions of Three Generations of Single-Crystal Superalloys (Wt%).**

Alloy	Cr	Co	Mo	W	Ta	Re	V	Nb	Al	Ti	Hf	Density		
												Ni (kg/dm <sup>3</sup> )	Ref.	
<b>First Generation</b>														
PWA 1480	10	5	-	4	12	-	-	-	5.0	1.5	-	Bal.	8.70	Gell et. al.
PWA 1483	12.8	9	1.9	3.8	4	-	-	-	3.6	4.0	-	Bal.	-	Duhl, D.N. and Gell, M.L.
René N4	9	8	2	6	4	-	-	0.5	3.7	4.2	-	Bal.	8.56	Wukusick, C.S.; Holmes, J.W. and O'Hara, K.S.
SRR 99	8	5	-	10	3	-	-	-	5.5	2.2	-	Bal.	8.56	Goulette, M.J. et al; Ford, D.A. and Arthey, R.P.
RR 2000	10	15	3	-	-	-	1	-	5.5	4.0	-	Bal.	7.87	Goulette, M.J. et al; Ford, D.A. and Arthey, R.P.
AM1	8	8	2	6	9	-	-	-	5.2	1.2	-	Bal.	8.59	Bachelet, E. and Lamanthe, G.
AM3	8	6	2	5	4	-	-	-	6.0	2.0	-	Bal.	8.25	Khan, T. and Brun, M.
CMSX-2*	8	5	0.6	8	6	-	-	-	5.6	1.0	-	Bal.	8.56	Harris, K. and Erickson, G.L.
CMSX-3*	8	5	0.6	8	6	-	-	-	5.6	1.0	0.1	Bal.	8.56	Harris, K. and Erickson, G.L.
CMSX-6*	10	5	3	-	2	-	-	-	4.8	4.7	0.1	Bal.	7.98	Harris, K. and Erickson, G.L.
AF 56 (SX 792)	12	8	2	4	5	-	-	-	3.4	4.2	-	Bal.	8.25	Doner, M. and Heckler, J.A.
SC 16	16	-	3	-	3.5	-	-	-	3.5	3.5	-	Bal.	8.21	Khan, T. and Caron, P.
CMSX*-11B	12.5	7	0.5	5	5	-	-	0.1	3.6	4.2	0.04	Bal.	8.44	Erickson, G.L.
CMSX*-11C	14.9	3	0.4	4.5	5	-	-	0.1	3.4	4.2	0.04	Bal.	8.36	Erickson, G.L.
<b>Second Generation</b>														
CMSX-4*	6.5	9	0.6	6	6.5	3	-	-	5.6	1.0	0.1	Bal.	8.70	Harris, K. and Erickson, G.L.
PWA 1484	5	10	2	6	9	3	-	-	5.6	-	0.1	Bal.	8.95	Cetel, A.D. and Duhl, D.N.
SC 180	5	10	2	5	8.5	3	-	-	5.2	1.0	0.1	Bal.	8.84	Nguyen-Dinh, X.
MC2	8	5	2	8	6	-	-	-	5.0	1.5	-	Bal.	8.63	Caron, P. and Khan, T.
René N5	7	8	2	5	7	3	-	-	6.2	-	0.2	Bal.	NA	Wukusick, C.S. and Buchakjian, Jr., L.
<b>Third Generation</b>														
CMSX*-10	2	3	.4	5	8	6	-	.1	5.7	.2	.03	Bal.	9.05	Erickson, G.L.
René N6	4.2	12.5	1.4	6	7.2	5.4	-	-	5.75	-	.15	Bal.	8.98	Walston, W.S. et. al.

level (vs. 1 ppm in other CM product) is thought attributable to the alloys' relatively high Ti content. Although the developmental heat gas contents are higher than the other CM experience, they nonetheless have not adversely affected SX casting yields when measured in terms of defect formation tendency and/or non-metallic inclusion content. Furthermore, production alloy manufacture will likely provide improvement to each characteristic.

**Table IV**  
**Typical Tramp Element Levels in Development Heats of the CMSX-11B and CMSX-11C Alloys.**


Alloy	Element/Concentration						
	C ppm	B ppm	Zr ppm	S ppm	N ppm	O ppm	SI wt. %
CMSX*-11B	20	<20	<10	1	.4	4	<.01
CMSX*-11C	20	<20	<10	1	4	4	<.01

**Foundry and Heat Treatment Characteristics**

Through October 1996, the CMSX-11B and CMSX-11C alloys have been cast successfully in six investment casting foundries located throughout the world. Items cast include test bars to 26 mm diameter, test slabs of varying size, plus both aero-turbine and industrial turbine blade components. Better than forty investment cast molds have been produced.

Through this experience, it is clear that both CMSX-11 alloy derivatives provide excellent SX castability. The alloys are not prone to formation of SX process defects such as freckles, slivers,

high or low angle boundaries and/or stray grain formation. High production product yields are anticipated since every developmental mold produced has output nearly 100% satisfactory product. Moreover, no cleanliness problems, as measured through zygo dye penetrant inspection and metallographic observation, have been experienced. An example of one of the test casting configurations utilized in the development is provided in Fig. 5. The industrial turbine blade test configurations are considerably larger, with heavy platform/root-section blades to about 250mm length being successfully cast.

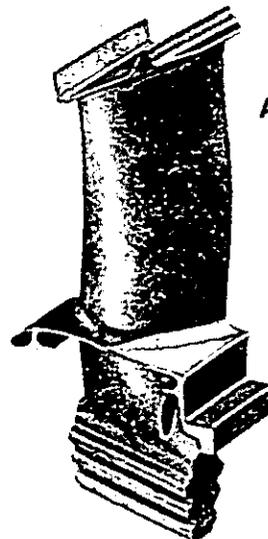


**Allison AE 2100 2nd Stage Blade.**

**Figure 5 - One of the several turbine blade configurations used to characterize the CMSX-11B and CMSX-11C alloy castability.**


The test articles and components produced are solution heat treated and given a three step aging treatment. Slightly different peak solution heat treatment temperatures are employed for the CMSX-11B and CMSX-11C alloys. Both treatments, however, can be accomplished in 10 hours or less. Primary aging (pseudo coating treatment aging) is undertaken at 1121°C/5 Hrs./AC condition for both alloys. Similarly, both alloys are further aged at 871°C/24 Hrs./AC + 760°C/30 Hrs./ AC condition.

The typical CMSX-11B and CMSX-11C fully heat treated microstructures are illustrated in Figs. 6 and 7, as well as the

specific respective solution heat treatments currently utilized. The respective solution heat treatments effect nearly 100%  $\gamma'$  and eutectic  $\gamma$ - $\gamma'$  dissolution, while the primary aging treatments result in  $\gamma'$  growth and arrangement into fairly regularly aligned, cubic  $\gamma'$  precipitates of about 0.4 - 0.5  $\mu\text{m}$  edge dimension. The secondary and tertiary aging treatments, as shown in Fig. 8 for CMSX-11B, tend to promote the formation of relatively fine matrix channel  $\gamma'$  precipitates which likely enhance strength in blade root sections, since root section temperature exposures are generally lower than 760°C.

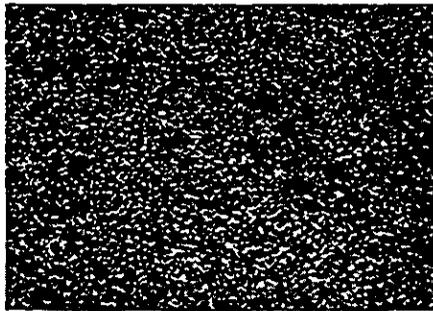

— .25 $\mu\text{m}$

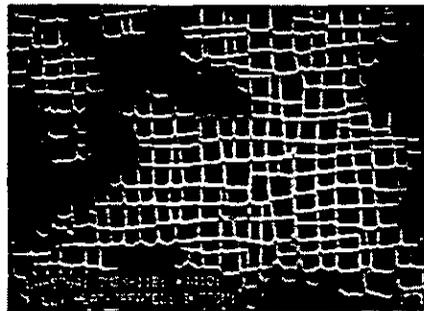


— 1 $\mu\text{m}$


Figure 6 - Two views of fully heat treated CMSX-11B alloy.

Solution: 1227°C/1 Hr. + 1249°C/1 Hr.  
+ 1260°C/2 Hrs. + 1264°C/4 Hrs./AC.

Age: 1121°C/ 5 Hrs./AC.  
871°C/24 Hrs./AC.  
760°C/30 Hrs./AC.

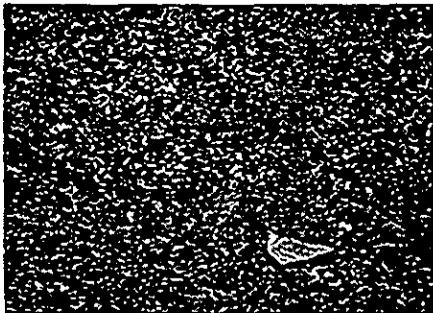

— .25 $\mu\text{m}$

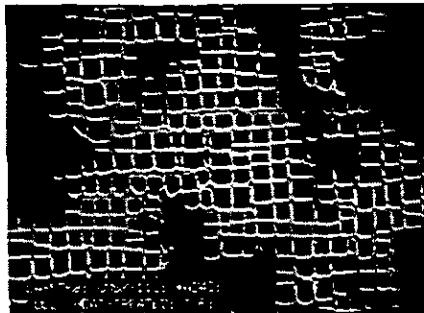

— 1 $\mu\text{m}$

Figure 7 - Two views of fully heat treated CMSX-11C alloy.

Solution: 1204°C/1 Hr.. + 1227°C/1 Hr.  
+ 1250°C/2 Hrs. + 1256°C/4 Hrs./AC.

Age: 1121°C/ 5 Hrs./AC.  
871°C/24 Hrs./AC.  
760°C/30 Hrs./AC.



a.

— 500 nm



b.

— 100 nm



c.

— 100 nm

Figure 8 - The CMSX-11B alloy aged at (a) 1121°C, (b) 1121°C + 871°C, and (c) 1121°C + 871°C + 760°C.

## MECHANICAL PROPERTIES

The results of fairly extensive creep-rupture testing undertaken at various stress levels, with temperature ranging 760-1038°C, show the CMSX-11B and CMSX-11C alloys develop impressive respective strength levels. The strengths of the materials are at least as good as commercialized SX casting alloys such as CMSX-2/3, PWA 1480 and René N4, plus as good or better, in certain tests, than stress-rupture strengths typically exhibited by the second generation, 3 wt. % Re containing CMSX-4, PWA 1484 and René N5 alloys.

Figure 9 illustrates the typical CMSX-11B/11C alloy strength in comparison to the DS René 80 and equiaxed IN 939 alloys. For a running stress of about 138 MPa, the CMSX-11 derivatives exhibit about 92°C greater strength than IN 939. Also indicated are the 871°C and 982°C capabilities of the PWA 1483 alloy (Duhl and Gell, 1981).

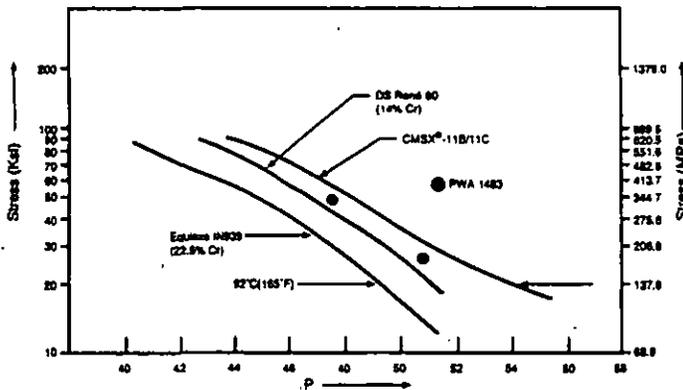


Figure 9 - Average longitudinal Larson-Miller stress-rupture strength of several alloys.

While Fig. 9 compared the CMSX-11B/11C materials to IN 939, DS René 80 and PWA 1483, Fig. 10 illustrates the materials' advantage over the SC 16 alloy, an IN 738 SX alloy derivative developed by ONERA for the European Community Collaborative COST program (Khan and Caron, 1990). At about 207 MPa stress, the SC 16 alloy deficit is about 44°C and at 138 MPa, approximately 64°C. If compared on the basis of 1% creep strength, the SC 16 alloy exhibits an even greater deficit. Others have shown that the SC 16 creep strength is similar to equiaxed IN 738 (Goldschmidt, 1994).

As illustrated in Table III, the densities of the CMSX-11B and CMSX-11C alloys are moderately low in comparison to other commercially utilized DS and SX casting alloys. Figure 11 illustrates the specific or density corrected strengths of several commercial alloys in comparison to the CMSX-11 materials. Perhaps of most significance, the CMSX-11B alloy's strength is shown to equal or exceed that of CMSX-4, while the higher Cr containing CMSX-11C alloy appears superior to CMSX-4 only at higher temperatures such as 982-1038°C.


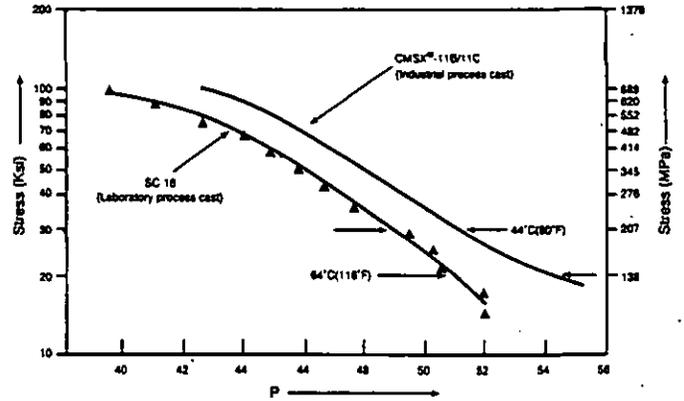


Figure 10 - Average longitudinal Larson-Miller stress-rupture strength of three alloys.

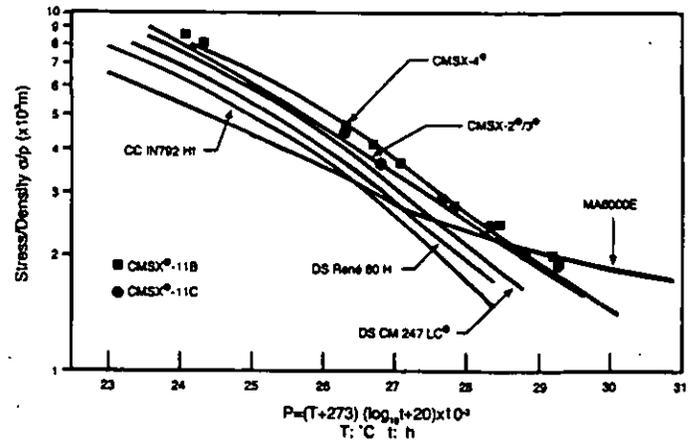

Base data provided by collaborating turbine engine producer.

Figure 11 - Density corrected stress-rupture strength of several alloys.

Along this line, non-density-corrected log stress vs. log time rupture strength comparison of the IN 738 LC, DS CM 247 LC, CMSX-4 and CMSX-11B alloys at 982°C is shown in Fig. 12. Interestingly, the non-Re containing CMSX-11B alloy is shown to exceed the CMSX-4 alloy's rupture strength for tests run to between 1500-2000 hours life. Although not shown, the CMSX-11B alloy 1% average creep strengths demonstrated in these tests were not quite as good as the averaged CMSX-4 capability, however, two of the four test results did not lag significantly. Similarly, Fig. 13 compares the log stress vs. log rupture life of CMSX-4 and CMSX-11B for tests performed at 1038°C (also without density correction), and illustrates a significant advantage occurring with CMSX-11B for a test run to about 3000 hours. As comparative CMSX-4 alloy creep data is not available for the given test, future efforts will define the CMSX-4 alloy's creep-rupture characteristic, as well as expand the CMSX-11B data base in the 1038°C - 1100°C temperature regime.

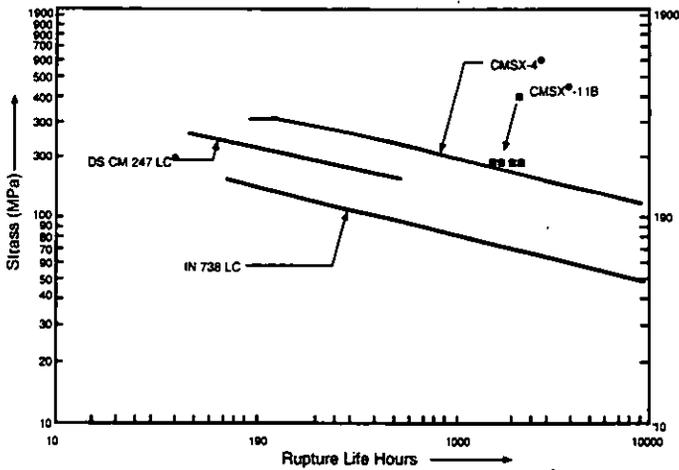


Figure 12 - 982°C stress-rupture strength of several alloys.


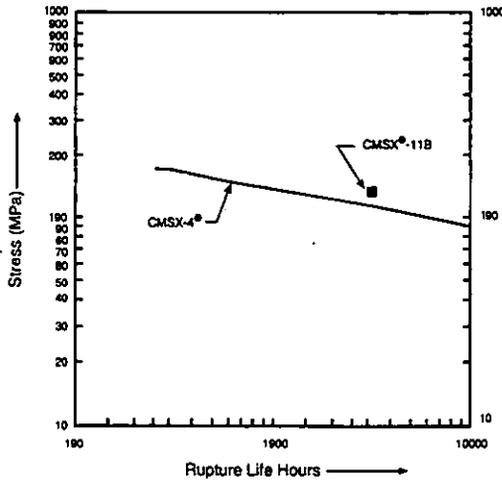


Figure 13 - 1038°C stress-rupture strength comparison of CMSX-11B and CMSX-4.

Figure 14 illustrates the CMSX-11B  $\gamma'$  structure for a specimen tested at 1010°C/103 MPa condition and which ruptured at 17,278.8 hours. Fracture and thread section views are presented, with both illustrating an absence of TCP phase. This absence of TCP is significant since Re-containing alloys generally form TCP under similar condition and exposure time. Interestingly, this individual rupture result is near the extrapolated life prediction which could be made for the CMSX-10 alloy tested at identical condition.

A review of superalloy 10,000 hour rupture strength capability, on the basis of alloy chromium content, is presented in Fig. 15. While traditional superalloy experience suggests that higher alloy chromium levels are accompanied by lower alloy strength, the CMSX-11B and CMSX-11C materials are shown to exhibit uniquely high relative strengths for their 12.5 and 14.5% respective Cr levels. Of particular significance is the positive strength comparison with the second generation, 3 wt. % Re containing superalloys such as PWA 1484 and CMSX-4. The data also illustrates that Re containing SX superalloys don't

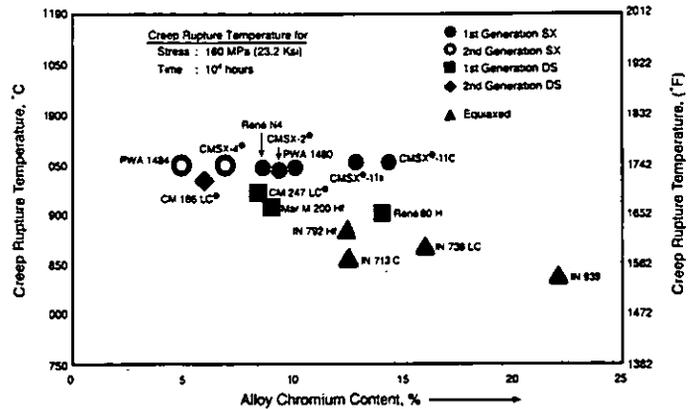


Base data provided by collaborating turbine engine producer.

Figure 15 - 10,000 hour rupture strength of several alloys.



Fracture Section

— 10 $\mu$ m

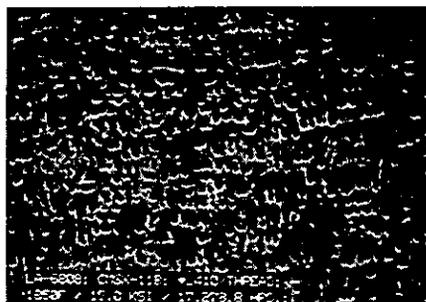

Thread Section

— 10 $\mu$ m

Figure 14 - Two post-test views of a CMSX-11B alloy specimen tested at 1010°C/103 MPa condition to rupture at 17,278.8 hrs.

necessarily provide long-term rupture strength advantages since other non-Re containing SX alloys such as René N4, CMSX-2 and PWA 1480 apparently perform similarly for 10,000 hour rupture life at the 160 MPa stress level, as determined through 1000 to 3000 hour rupture data extrapolation undertaken by a collaborating gas turbine engine producer.

While data extrapolation can lead to faulty conclusions, the extrapolations presented in Fig. 15 are given support through the work of Ross and O'Hara (1996), presented in Fig. 16. This figure illustrates the results of rupture tests performed at 982°C for lives to 10,000 hours. The results presented for René N4 in comparison to other 1st, 2nd and 3rd generation SX alloys show the non-Re containing René N4 alloy rupture performance equaling and exceeding their 2nd generation SX alloy strength through the 2,000 - 10,000 hour rupture test results.

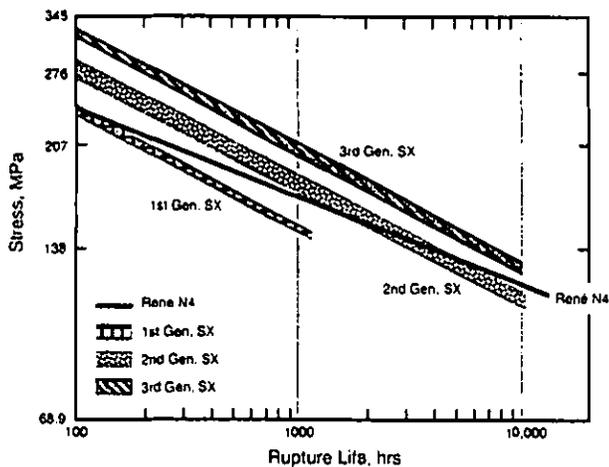


Figure 16 - 982°C Long Time Rupture Behavior of René N4 vs. Other Single Crystal Superalloys (Ross, E. W. and O'Hara, K. S., 1996)

### ENVIRONMENTAL PROPERTIES

Environmental tests performed on superalloy materials often give rise to varied results, depending on methods employed and sources employed. In this investigation, four different turbine producers performed both hot corrosion and oxidation tests on the CMSX-11 alloy derivatives. The tests performed were undertaken by both burner rig and crucible evaluation methods, with the significance of the results comparing favorably between three of the four investigative sources, thereby lending credibility to the results achieved.

Figure 17 illustrates the derivative alloys' 500 hour hot corrosion characteristics determined in comparative crucible tests undertaken at 750°C, 850°C and 900°C. Similarly, Figs. 18 and 19 present results of hot corrosion tests performed at 732°C and 899°C, with comparison to the IN 738 LC alloy capability. The results appear to confirm that the CMSX-11 materials behave similar to the IN 738 LC material with exposure at around 750°C, and that with long term exposure at about 900°C, the higher Cr

containing derivative, CMSX-11C, exhibits an advantage vs. the CMSX-11B alloy, while continuing to perform as well as IN 738 LC to at least 2400 hours.

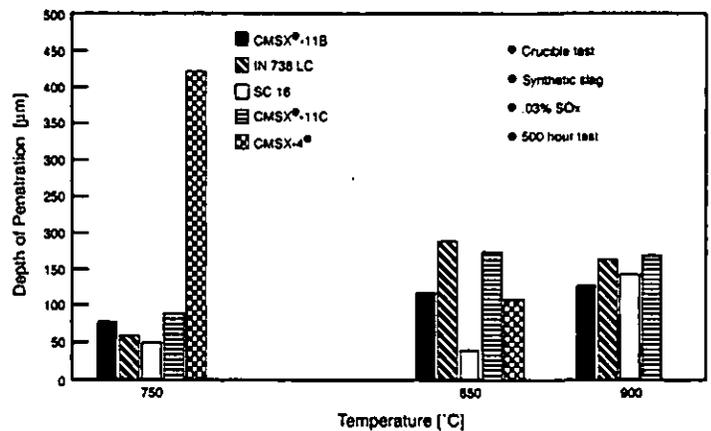


Figure 17 - Hot corrosion of various alloys at 750, 850 and 900°C.

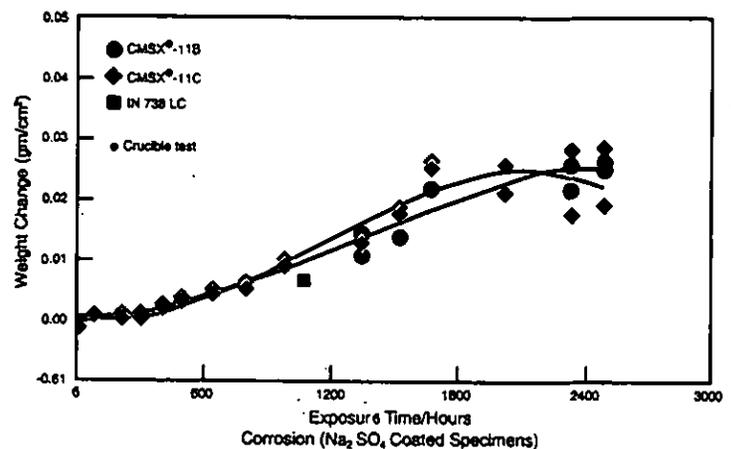


Figure 18 - 732°C cyclic hot corrosion of several alloys.

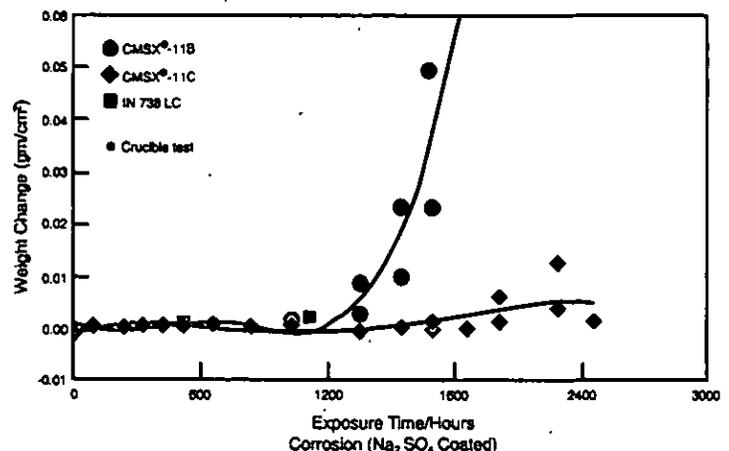


Figure 19 - 899°C cyclic hot corrosion of several alloys.

The results of extremely aggressive burner rig hot corrosion tests performed to 500 hour duration at 1050°C are shown in Fig. 20. Hot corrosion results are presented through comparison to other widely used gas turbine alloys such as FSX-414, DS René 80 H, DS IN 738 LC, DS IN 939 and DS CM 186 LC. The actual corrosion results are presented in terms of test specimen thickness loss, while the respective material's strength capabilities are expressed on the figure's y-axis as creep-rupture temperature capabilities for 1000 hour lives with a testing stress of 284.4 MPa. For this testing, the figure illustrates that the CMSX-11C alloy develops DS René 80 - type hot corrosion resistance with an attendant 25°C strength advantage. The CMSX-11B alloy doesn't provide quite as good hot corrosion capability in the test, but is significantly better than the DS CM 186 LC alloy, a material also considered for some industrial turbine applications.

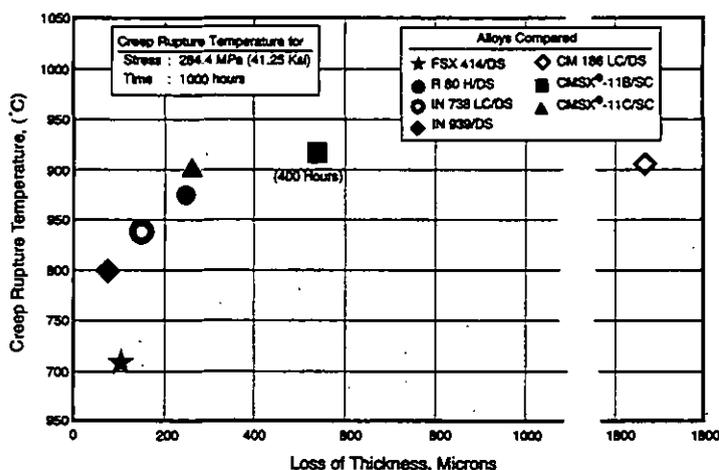


Figure 20 - Alloy strength and 1050°C/500 hour burner rig hot corrosion comparison of several alloys.

Burner rig oxidation test results are shown in Fig. 21. The alloys compared (along with the result presentation methods employed) are identical to those presented in Fig. 20. For this run at 1200°C and exposure of 500 hours, the CM 186 LC alloy is shown to exhibit the best alloy oxidation resistance, with the CMSX-11B and CMSX-11C materials behaving quite similarly; a unique capability for materials exhibiting IN 738/IN 792/ René 80 type corrosion resistance. To that point, Fig. 21 also exhibits the reduced oxidation resistance of the René 80 and IN 738 LC alloys in comparison to CMSX-11.

Confirmation of the CMSX-11 oxidation characteristic is provided in Fig. 22 where the results of a cyclic crucible test performed at 1000°C on the CMSX-11B, CMSX-11C and IN 738 LC alloys are presented. While the IN 738 LC alloy oxidation resistance is low, the two CMSX-11 alloy derivatives exhibit relatively good oxidation characteristic for the duration of the test, i.e., 3000 hours. While not presented, the Fig. 22 test data source has developed unpublished data at identical conditions for

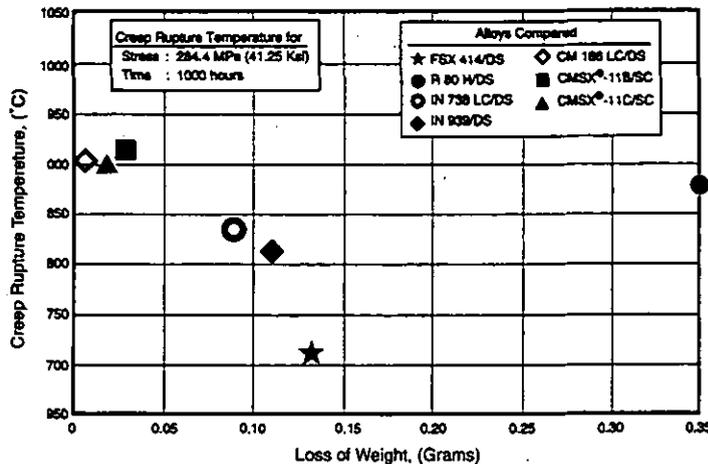


Figure 21 - Alloy strength and 1200°C/500 hour burner rig oxidation comparison of several alloys.

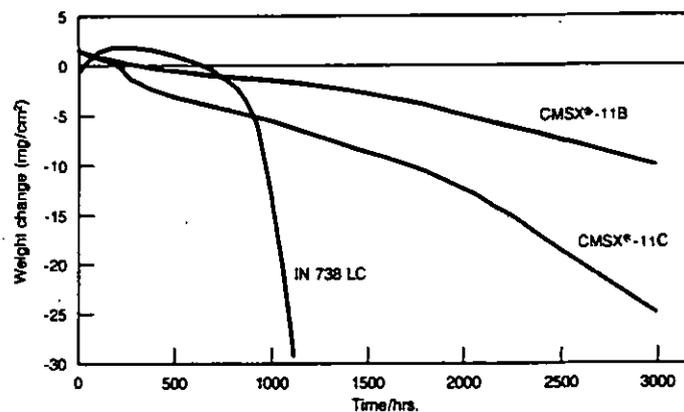


Figure 22 - 1000°C cyclic oxidation of three alloys.

the PWA 1483 alloy which show its capability appearing between the IN 738 LC and CMSX-11C test results. Similar oxidation testing undertaken at 1010°C at another turbine builder shows similar results for the CMSX-11 alloys, as illustrated in Fig. 23.

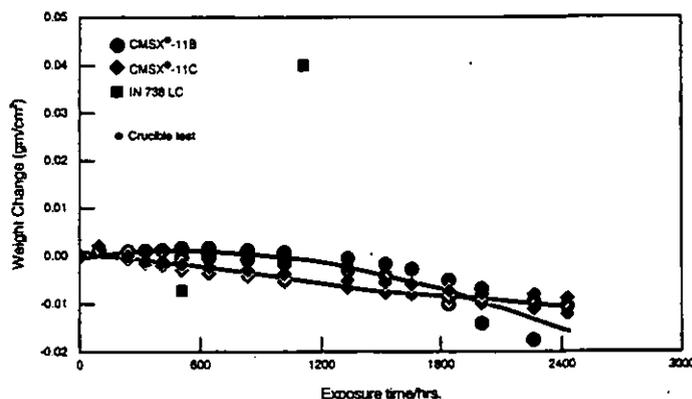


Figure 23 - 1010°C cyclic oxidation of three alloys.

The alloys, therefore, provide surprisingly good oxidation characteristics, as confirmed through both burner rig and crucible tests performed by multiple gas turbine engine manufacturers. At the same time, similar multiple source testing confirms both alloys exhibit very good hot corrosion capabilities (IN 738 LC/René 80/IN 792 level). The ability of the CMSX-11B and CMSX-11C alloys to provide good hot corrosion and oxidation characteristics, in tandem, is thought unique among available turbine materials.

## SUMMARY

Two unique single crystal casting superalloys have been developed for gas turbine engine blade and/or vane application where demanding strength and environmental issues prevail. The non-rhenium containing alloys, CMSX-11B and CMSX-11C, exhibit short-term creep rupture strengths which are as good or better than other lower chromium-containing, first generation SX superalloys. Moreover, both alloys develop long-term (greater than 1000 hours duration) stress-rupture strengths which are as good or better than Re-containing second generation SX alloys at conditions pertinent to gas turbine blade and vane component operation. Furthermore, the CMSX-11B and CMSX-11C alloys also provide uniquely attractive blends of bare hot corrosion and oxidation resistance; a characteristic thought unique among superalloys commercially available.

## Acknowledgment

The invaluable assistance of several turbine engine companies, who wish to remain unidentified at this point, is gratefully acknowledged.

## REFERENCES

- Bachelet, E. and Lamanthe, G., 1986, Paper presented at the National Symposium on SX Superalloys, Viallard-de-Lans, France 26-28 February 1986.
- Barker, Thomas, 1995, "Siemens' New Generation," *Turbomachinery International*, January/February 1995, pp. 20-22.
- Caron, P. and Khan, T., 1989, "Development of a New Nickel Based Single Crystal Turbine Blade Alloy for Very High Temperatures," *Euromat '89*, pp. 333-338.
- Cetel, A.D. and Duhl, D.N., 1988, "Second Generation Nickel-Base Single Crystal Superalloys," *Proceedings; Superalloys 1988*, D.N. Dhul et al., ed., The Minerals, Metals and Materials Society, 1988, pp. 235-244
- Doner, M. and Heckler, J.A., 1985, Paper presented at the *Aerospace Tech. Conf.*, Long Beach, CA, October 1985.
- Duhl, D.N. and Gell, M.L., 1981, United Technologies Corporation, G.B. patent 2112812A—PWA 1483 Alloy.
- Erickson, G.L., 1994, Cannon-Muskegon Corporation, U.S. patent 5,366,695—CMSX-10 Alloy.
- Erickson, G.L., 1994, "Superalloy VIM and EBCHR Processes," *International Symposium on Liquid Metal Processing and Casting* (Santa Fe, New Mexico).
- Erickson, G.L., 1996, Cannon-Muskegon Corporation, U.S. patent 5,489,346—CMSX-11B Alloy.
- Erickson, G.L., 1997, Cannon-Muskegon Corporation, U.S. patent pending—CMSX-11C Alloy.
- Farmer, Robert, 1993, "First V84.3 to Met Ed for Joint 'B.O.T.' Demo Project," *Gas Turbine World*, July/August 1993, pp. 24-33.
- Farmer, Robert, 1995, "See 57% net efficiency combined cycles powered by 2400°F '3A' series turbines," *Gas Turbine World*, January/February 1995, pp. 18-28.
- Ford, D.A. and Arthey, R.P., 1984, "Development of Single-Crystal Alloys for Specific Engine Application," *Proceedings Superalloys 1984*, Gell et al., ed., The Minerals, Metals and Materials Society, pp. 115 - 124.
- Gell et al., 1980, "The Development of Single Crystal Turbine Blades," *Proceedings, Superalloys 1980*, Tien, J. K. et al., ed., The Minerals, Metals, and Materials Society, 1980, pp. 205-214.
- Goldschmidt, D., 1994, "Single Crystal Blades," *Materials for Advanced Power Engineering* (Kluwer Academic Publishers), pp. 661-674.
- Goulette et al., 1984, "Cost Effective Single Crystals", *Proceedings, Superalloys 1984*, Gell et al., ed., The Minerals, Metals, and Materials Society, 1984, pp. 167-176.
- Harris, K. and Erickson, G.L., 1986, Cannon-Muskegon Corporation, U.S. patent 4,582,548—CMSX-2 Alloy.
- Harris, K. and Erickson, G.L., 1987, Cannon-Muskegon Corporation, U.S. patent 4,643,782—CMSX-4 Alloy.
- Harris, K. and Erickson, G.L., 1988, Cannon-Muskegon Corporation, U.S. patent 4,721,540—CMSX-6 Alloy.
- Holmes, J.W. and O'Hara, K.S., 1988, *ASTM STP 942* (Philadelphia, PA: ASTM), pp. 672-691.
- Independent Power Report*, 1992, "G.E. Forecasts Worldwide Plant Orders of 925,000 MW Between now and 2001," July 1992, p. 1, 3.
- Khan, T. and Brun, M., 1989, *Symp. on SX Alloys* (Munich/Germany: MTU/SMCT, June 1989).
- Khan, T. and Caron, P., 1990, "Development of a New Single Crystal Superalloy for Industrial Gas Turbine Blades," *High Temperature Materials for Power Engineering*, 1990 (Kluwer Academic Publishers), pp. 1261-1270.
- Nguyen-Dinh, X., 1990, Allied Signal, Inc., U.S. patent 4,935,072—SC 180 Alloy.
- Ross, E. W. and O'Hara, K. S., 1996, "René N4: A First Generation Single Crystal Turbine Airfoil alloy With Improved Oxidation Resistance, Low Angle Boundary Strength and Superior Long Time Rupture Strength," *Proceedings, Superalloys 1996*, R. D. Kissinger et al., ed., The Minerals, Metals and Materials Society, 1996, pp. 19-25.

Sims, Chester T., 1989, private communications during technical meeting at Cannon-Muskegon.

Stambler, Irwin, 1995, "Technology base in place for next phase of ATS development program," *Gas Turbine World*, September/October 1995, pp. 10-14.

*Turbomachinery International*, 1994 a, "ABB's New Gas Turbine Decouple Efficiency and Temperature," January/February 1994, pp. 20-24.

*Turbomachinery International*, 1994 b, "Future Gas Turbines for Power Generation," January/February 1994, pp. 30-31.

*Turbomachinery International Handbook*, 1994, "Turbine Market Forecast, 1994 to 2003," pp. 31-34.

Walston, W.S. et al., General Electric Company, U.S. patent 5,455,120—René N6 Alloy.

*World Power Systems Intelligence*, 1993, "Advanced Turbine Systems: Follow-up," Issue No. 179, pp. 6-7.

Wukusick, C.S., 1980, Final Report NAVAIR/N62269-78-C-0315, 25 August 1980.

Wukusick, C.S., Buchakjian, Jr., L., 1991, General Electric Company, U.K. patent application GB 2 235 697 A. Published March 13, 1991 "Improved Property-Balanced Nickel-Base Superalloy for Producing Single Crystal Articles."