

Comparative evaluation of conventional and microwave hydrothermal carbonization of human biowaste for value recovery

Oluwasola O. D. Afolabi and M. Sohail

ABSTRACT

This paper compares conventional and microwave hydrothermal carbonization (HTC) of human biowaste (HBW) at 160 °C, 180 °C and 200 °C as a potential technology to recover valuable carbonaceous solid fuel char and organic-rich liquor. Also discussed are the influence of HTC heating methods and temperature on HBW processing conversion into solid fuel char, i.e. yield and post-HTC management, dewaterability rates, particle size distribution and the carbon and energy properties of solid fuel char. While HTC temperatures influenced all parameters investigated, especially yield and properties of end products recovered, heating source effects were noticeable on dewatering rates, char particle sizes and HBW processing/end product recovery rate and, by extension, energy consumed. The microwave process was found to be more efficient for dewatering processed HBW and for char recovery, consuming half the energy used by the conventional HTC method despite the similarity in yields, carbon and energy properties of the recovered char. However, both processes reliably overcame the heterogeneity of HBW, converting them into non-foul end products, which were easily dewatered at <3 seconds/g total solids (TS) (c.f. 50.3 seconds/g TS for a raw sample) to recover energy-densified chars of ≈ 17 MJ/kg calorific value and up to 1.4 g/l of ammonia concentration in recovered liquor.

Key words | bioenergy, chars, conventional heating, hydrothermal carbonization, microwave, sewage sludge

Oluwasola O. D. Afolabi (corresponding author)

M. Sohail

School of Civil and Building Engineering,

Loughborough University,

Loughborough LE11 3TU,

UK

E-mail: o.o.d.afolabi2@lboro.ac.uk

INTRODUCTION

The need for more innovative approaches to ameliorate the pervasive consequences of poor sanitation in low- and middle-income countries cannot be over-emphasized, as 2.4 billion people still lack access to safe sanitation. An estimated 1 billion tons of faecal matter is generated annually (Sobsey 2006). In low- and middle-income countries, more than 90% of faecal waste generated is discharged untreated (Langergraber & Muellegger 2005). Current approaches such as manual pit emptying, incineration, and disposal to landfill present significant environmental problems related to public health, environmental pollution, greenhouse emissions and contamination of soil and water resources (Strauss & Montangero 2002; Samolada & Zabaniotou 2014; WHO/UNICEF 2014). Environmental regulations for disposal, meanwhile, are becoming increasingly severe and call for more effective solutions and management strategies. The

potential for integrating novel sanitation transformative technologies to address the challenges of poor sanitation is gaining international attention and relevance. This interest also lies with their being potentially more environmentally friendly, aligning with the concepts of sustainable ecological sanitation, and favouring valuable resource recovery and bioenergy generation (Esrey 2001; Samolada & Zabaniotou 2014). Essentially, sanitation technologies should not only treat human faecal wastes without any health or environmental impacts and recover valuable (energy) end products, but should also be scalable to address rapid increases in population and urbanization, without violating environmental regulations and standards for faecal management.

The hydrothermal carbonization (HTC) process, sometimes referred to as 'wet pyrolysis', represents an effective

sanitation technology that can be used to address both issues, i.e. poor sanitation and bioenergy needs. HTC can be used to process human biowaste (HBW) – untreated excrement, faecal sludge, primary and secondary sewage sludge (SS) – into a sterilized safe form, while also recovering usable and valuable organic carbon, nitrogen and energy end products. HTC is a thermochemical process that involves heating biowaste at sub-critical water conditions between 160 °C and 220 °C under autogenous pressure in the absence of oxygen, to convert biowaste organics into valuable end products – a carbonaceous (coal-like) solid, i.e. char, and organic-rich liquor (Peterson *et al.* 2008; Libra *et al.* 2011; Basso *et al.* 2016). HTC is distinguished by the use of wet feedstock, obviating the need for energy-intensive drying before or during the process (Libra *et al.* 2011); essentially, this makes HBW, which is characterized by high moisture content of up to 95% (w/w), fit the HTC spectrum. Further, the capacity for handling the heterogeneous nature of HBW pathogen kill (due to the high temperature associated with the technology), and the potential recovery and recycling of valuable nutrients, energy and other inorganic chemicals (in ionic forms), strengthens the HTC technology (Peterson *et al.* 2008; Libra *et al.* 2011).

Heating source/method and processing efficiencies are very important considerations for any waste processing technology. A variety of heat sources used for HTC processing have been reported. Conventional HTC (C-HTC) processes usually involve the use of electrically heated high-pressure stainless steel vessels/reactors where heating is achieved via temperature gradients, with conduction and convection as the main heat-transfer mechanisms (Ramke *et al.* 2009; Berge *et al.* 2011; Mäkelä *et al.* 2015). Microwave HTC (M-HTC), i.e. heating via the electromagnetic interaction of microwave with dipolar materials (mainly water content in HBW), has also been acknowledged (Guiotoku *et al.* 2009; Afolabi *et al.* 2015; Eliagwu & Greenway 2016). Absent from the literature, however, is an assessment of how both heating methods compare under similar HTC temperature ranges and how they affect the whole HBW processing/conversion into solid char fuel. More specifically, there are knowledge gaps in comparative char yield (and energy consumed during both HTC processes); post-HTC processes, including dewaterability rates of processed HBW, particle size distribution (PSD) of char solids, as well as their carbon and energy properties; and ammonia recovery and other HTC liquor properties. These knowledge gaps informed the present study as part of our continued research under the Bill and Melinda Gates Foundation ‘Reinvent the Toilet’ project, which centres on the development

of an HTC-based sanitation facility/toilet that collects HBW, and treats and converts it into safe and usable products.

MATERIALS AND METHODS

Primary SS

Primary SS, the closest alternative to fresh human faeces, is used for this study as representative of an HBW sample. This was obtained from the primary sedimentation holding tank at Wanlip sewage treatment works, Leicester, UK. The SS derives from a catchment area serving a population of 0.5 million people, with mixed domestic and industrial effluent. The SS was obtained in a container that was vented to prevent gas build-up. Once sealed, the SS was transported for storage in the cold room of the Civil Engineering Water Laboratory throughout the experimental period. The characteristics of the SS used for this study are summarized in Table 1.

HTC methods

M-HTC

The M-HTC was set up as reported in a previous study (Afolabi *et al.* 2015) using Anton Paar Multiwave Microwave

Table 1 | Characteristic of SS used in this study

Parameters	Primary SS
Elemental (%)	
Carbon, C	36.6 ± 0.4
Hydrogen, H	5.7 ± 0.04
Nitrogen, N	5.1 ± 0.03
Oxygen, O ^a	52.6 ± 0.5
Proximate (%)	
Moisture content, MC (%)	95.6 ± 0.2
TS (%)	4.4 ± 0.1
VS (of TS)	71.4 ± 0.2
FS (of TS)	28.6 ± 0.2
pH	5.5 ± 0.3
Energy content (MJ/Kg)	15.8 ± 0.2
Density ^b (g/cm ³)	1.1
CST (seconds)	389.9 ± 28.9

^aDetermined by difference, i.e. [100 – (C + H + N)]%.

^bProvided by the waste treatment plant.

Labstation (Anton Paar Ltd, Austria) at 2.45 GHz frequency, 900 W at 10A pulse-controlled power output. Raw SS (total weight 160 g) was equally divided in four replicates and poured into pre-weighed cylindrical PTFE-TFM reactor vessels of 260 °C and 60 bars rating. Weighing was by mass to improve reproducibility during each carbonization experiment. The reactor vessels were loaded symmetrically on the microwave carousel to enhance temperature and pressure reading accuracy during the carbonization process. Microwave energy supplied to the reactor vessels was controlled by wireless sensors, which monitor internal temperature and pressure inside the vessels and also prevent overheating. In addition, an infrared sensor at the base of the microwave cavity measured the temperature in all the reactor vessels and maintained the reactor vessels at ± 2 °C of set reaction temperature during the M-HTC process.

Conventional conduction hydrothermal carbonization (C-HTC)

The C-HTC process was conducted using a high-pressure reactor (Berghof Ltd, Germany) with a temperature and pressure rating of 300 °C and 200 bar. The reactor comprised a 300 ml PTFE reactor vessel placed in a stainless steel jacket, surrounded by a thermo-insulated heater (DAH-3) block mount. The stainless steel jacket was seated on a (BLH-800) electric heating plate (of a similar microwave power rating), which supplied heat to the reactor vessel by conduction. Raw SS (total weight 160 g) was poured inside the pre-weighed PTFE vessel and loaded into the stainless steel jacket. Weighing was also done by mass. The reaction temperature was measured via a thermocouple placed centrally within the PTFE reactor vessel and connected to a BTC-3000 regulator, which maintained a set reaction temperature during the C-HTC process. A PT-100 pressure sensor also measured autogenously generated pressure inside the vessel.

Experimental work-up

Raw SS was processed under both the M-HTC and C-HTC processes at three peak temperatures: 160 °C, 180 °C and 200 °C. The process pressure was autogenous and correlated with the carbonization temperature used. Guided by preliminary experiments and existing literature (Neyens & Baeyens 2003; Funke & Ziegler 2010; Guiotoku *et al.* 2011; Chen *et al.* 2012; Lu *et al.* 2012; Basso *et al.* 2015), 30 mins was used as residence time for the M-HTC process, while 3 hrs was used for the C-HTC process to ensure enough contact time

to achieve carbonization during each experiment. The experiments were conducted in triplicate. Using a wattmeter connected between the mains and each item of carbonization equipment, the energy consumed per gram of SS solids ($\text{Wh}\cdot\text{g}^{-1}$ TS) processed during each M-HTC and C-HTC processes were estimated for each HTC temperature investigated. After the completion of each carbonization experiment, the reactor vessels were cooled to room temperature. Carbonized materials were filtered using a 63 μm mesh sieve size. The solid fraction, i.e. the wet char, was subsequently dried at 105 °C for 18–24 hrs for further analysis. The char yield on a dried basis was estimated using Equation (1):

$$\text{Char yield}_{(db)}(\%) = \frac{\text{Dried char recovered, g}}{\text{Dried SS, g}} \times 100\% \quad (1)$$

The liquor fraction recovered was analyzed immediately after each carbonization experiment to minimize volatile losses.

Analysis and characterizations

Solids analysis

Raw SS samples and chars produced from both HTC methods were analyzed for moisture (MC), total solids (TS), volatile solids (VS) and fixed solids (FS) according to Standard Methods 2540G (APHA/AWWA/WEF 2005).

Dewaterability rate

The dewaterability rate was measured as capillary suction time (CST) according to Standard Method 2710G (APHA/AWWA/WEF 2005) using a CST apparatus (Triton-Type 165, Triton Electronic Ltd, UK). The experiment was conducted with a minimum of seven replicates, before estimating their mean values and standard deviations.

PSD analyses

PSD analysis of dried and uniformly ground solids of raw SS and chars from each experiment was conducted by the laser diffraction method on a Malvern Mastersizer 2000 (Malvern Instruments Ltd, UK) adopting Standard Method ISO 13320:2009. Depending on reproducibility of scattered particle patterns, a minimum of seven replicates were

conducted and the size distribution averages were analyzed using the PSD analyzer.

Elemental analysis

Raw SS samples and the chars recovered from each carbonization process were analyzed for their carbon (C), hydrogen (H) and nitrogen (N) contents using a CHN analyzer (CE-440 Elemental Analyzer, Exeter Analytical Inc., UK) adopting the [ASTM D5373-16](#) Standard Test Method. Analyses were conducted in triplicate, with mean values and the standard deviation estimated for each sample respectively.

Energy content

Calorific values, i.e. higher heating values (HHVs), of all dried solids (raw SS and chars recovered from each carbonization process) were measured using a bomb calorimeter (CAL 2K, Digital Data Systems, South Africa) based on the [ISO 1928:2009](#) Standard. Tests were conducted in triplicate and mean values used as the energy value of the samples.

Recovered HTC liquor analyses

The chemical oxygen demand (COD) of the HTC liquor recovered after separating solids was measured using standard test kits on a COD analyzer (Photometer 8000, Palintest Ltd, UK) according to Standard Methods 5229D (Close Reflux Calorimetric method) ([APHA/AWWA/WEF 2005](#)). Total organic carbon (TOC) was determined by the high-temperature combustion method using a TOC analyzer (DC 190 Rosemount Dohrman, USA) according to Standard Methods 5310B ([APHA/AWWA/WEF 2005](#)). An analysis of ammonia and volatile fatty acids (VFA) was conducted using standard test kits on an automatic spectrophotometer (Hach Lange DR 3900) adopting Standard Methods 4500-NH₃, Phenate Method and Spectrophotometric Method respectively ([APHA/AWWA/WEF 2005](#)). The pH was measured using an electronic pH meter (Mettler Delta 340), calibrated against freshly prepared solutions of known pH 4.0 and 7.0. All analyses were conducted in triplicate, with their mean and standard deviation estimated. These tests were conducted for comparative assessment of recovered liquor characteristics from both HTC methods.

RESULTS AND DISCUSSION

Physical and sensory assessment

The smell and colour of the carbonized SS recovered from both processes were very similar. Foul odour, a characteristic of raw SS, was completely eradicated and replaced with a coffee-like smell and a coal-like black colouration. These observations are consistent with previous studies involving thermochemical conversion/transformation processes at temperature ranges similar to those used in this study. For example, using a paar reactor supplied with heat from a muffle furnace, [Wilson & Novak \(2009\)](#) observed a caramel-like odour and tea-colouration of processed primary and secondary wastewater sludges processed at 130–220 °C. Other studies involving HTC processing of biowastes using plug flow reactors ([Peterson *et al.* 2010](#)), autoclave ([Lu *et al.* 2011](#)) and microwave pyrolysis ([Masek *et al.* 2013](#)) have all reported similar organoleptic changes. These changes are due to intermediate reactions associated with HTC processing at temperatures ≥ 160 °C, including Maillard reaction (occurring between amino acids monomers and carbonyl radicals of reducing sugars; both resulting from thermal hydrolyses of protein and carbohydrates components of SS during HTC processing) and caramelization reactions (a non-enzymatic browning effect on reducing sugars in biowastes) ([Nurtsen 2005](#); [Wilson & Novak 2009](#); [Peterson *et al.* 2010](#)). Effectively, the similarities in organoleptic properties of end products recovered from both HTC methods in this study compared to previous studies suggests that both processes converted SS to a more pleasant end product. Additionally, smell and colour transformations tend to occur regardless of type/source of heating source used, with reactions associated with HTC temperature processing playing a crucial role in eradicating the foul odour of HBW.

Dewaterability of processed HBW

CST quantifies the time required for sludgy water content drawn by capillary forces to wet a piece of adsorbent chromatography filter paper. A greater CST value indicates that it is more difficult for sludgy water to be drawn out by capillary forces, and implies higher resistance to filtration or poor dewaterability. As shown in [Table 2](#), dewaterability of carbonized HBW material is feasible using both the M-HTC and C-HTC process. Both processes indicated

Table 2 | CST (seconds) and S-CST^a (seconds/g TS) of processed SS under both HTC processes

Raw SS	CST (seconds)		S-CST (seconds/g TS)	
	M-HTC	C-HTC	M-HTC	C-HTC
	389.9 ± 28.9		50.3 ± 3.7	
160 °C	10.6 ± 0.5	15.8 ± 0.8	2.3 ± 0.1	3.4 ± 0.4
180 °C	9.3 ± 0.6	11.4 ± 0.6	2.2 ± 0.2	2.9 ± 0.1
200 °C	8.2 ± 0.4	10.5 ± 0.5	2.1 ± 0.2	2.8 ± 0.2

^aSpecific CST (seconds/g TS) = $\frac{\text{CST values (seconds)}}{\text{Total solids of sludgy material (dried weight, g)}}$

significant improvement in dewatering rates when compared to raw SS at all temperatures investigated.

Furthermore, dewaterability was even improved over the HTC carbonization temperature ranges used for both processes – the net effect being that the dewaterability rate of carbonized SS actually decreased with increasing temperature of carbonization. Comparatively, CST values for carbonized products by the M-HTC process at all temperature ranges examined were shorter than C-HTC – indicating a higher dewaterability. This effect, i.e. the improvement in dewaterability of M-HTC compared to the C-HTC method, was most significant at 160 °C (by 32.8%), but reduced towards 180 °C and 200 °C (<12%). These comparatively observed improvements are similar to those reported in a previous study: 13.8% and 17.8% improvements in dewatering rates of microwave pre-treated SS compared to those of conventionally heated sludge at 60 °C and 65 °C respectively (Pino-Jelcic *et al.* 2006). Solid concentration/distribution also affects CST values, because larger solid particles tend to block movement of water, which is driven through capillary forces (APHA/AWWA/WEF 2005). Specific CST (S-CST) was estimated, which allows the dewaterability of samples having various solid concentrations to be compared to understand the net effect of the HTC process on dewaterability. Effectively, M-HTC yields solid char that dewateres at ≤2.3 seconds/g TS, while the C-HTC yields at ≤3.4 seconds/g TS at temperatures above ca. 150 °C (c.f. raw SS at 50.3 ± 3.72 s g⁻¹ TS).

While both processes improved dewaterability of processed SS for char recovery, HTC temperature and heating methods can be implied to have influenced dewaterability. The aqueous phase of sludgy materials is generally described as free water and bound water; however, bound water requires higher energy to be released (Neyens & Baeyens 2003). Fundamentally, raising the temperature of sludgy materials

decreases their viscosity and facilitates filterability. This explains the net improvement in dewaterability rates observed under both processes as temperature (more energy) is raised from 160 °C to 200 °C. The thermal hydrolysis that occurs under both processes activates sludge flocs (which serve as repositories for water) to improve dewaterability, however under different mechanisms. Heat transferred through conduction and convection during C-HTC process disintegrates sludgy flocs (Xun *et al.* 2008). The C-HTC process relies on thermal gradients (from source of heating to the heated sludge) to dislodge larger sludge flocs, degrade the sludge floc structure and release bound water. However, sludge dewaterability under the M-HTC process can be attributed to both the thermal and athermal effects of microwave heating (Wojciechowska 2005; Eskicioglu *et al.* 2007), and possibly explains the relatively lower CST values obtained when compared with the C-HTC process. Thermal effects result from direct coupling of electromagnetic energy with water molecules and other polar organics in sludgy biowaste, causing rapid volumetric heating. Athermal effects, meanwhile, i.e. those not related to temperature, are attributed to the vibrational effects of microwaves on the hydrogen bonds in sludgy cell walls through the alternation of the electric field of water (polar substance), causing overall weakening; this may facilitate the breaking of chemically bound water in sludgy biowaste (Solymon *et al.* 2011). At all temperatures investigated, both (thermal and athermal) effects selectively energize polar substances within biowaste and chemically bound water in the cells of SS. This subsequently leads to rapid disruption and disintegration of sludge flocs and bound water, rupturing of the cell walls and membranes, accompanied by chemical dissociation and release of bound water.

In essence, improvements in dewaterability during M-HTC over C-HTC are due to the highly selective nature of the dielectric heating mechanism. Understanding of the degree/extent to which both effects (thermal and athermal) influence dewaterability is still developing, but may explain why M-HTC is slightly better than the C-HTC in this study.

PSD of recovered char fuel

The cumulative volume weighted distribution (%) profiles of particle sizes of both raw and carbonized chars produced from M-HTC and C-HTC at the different carbonization temperatures used are presented in Figures 1 and 2 respectively.

As shown in Figure 1, particle sizes in raw SS span a range up to 1,700 μm, whereas chars produced at the three

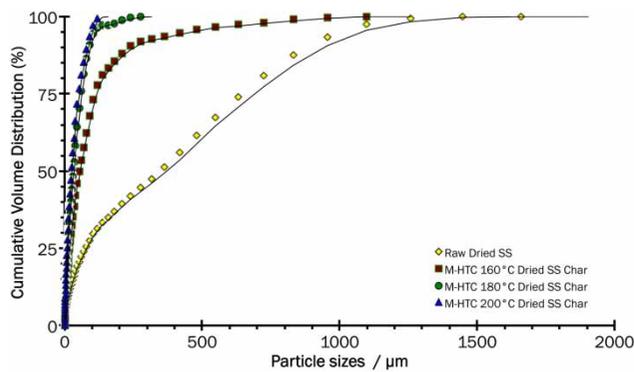


Figure 1 | PSD profiles of raw SS and chars from the M-HTC process.

carbonization temperatures from the M-HTC process produce a smaller and narrower percentage cumulative volume distribution of less than 300 μm at 180 $^{\circ}\text{C}$ and 200 $^{\circ}\text{C}$; 160 $^{\circ}\text{C}$ gave a range slightly above 1,000 μm . Similar behaviour was obtained with the C-HTC process (see Figure 2). However, for temperatures below 200 $^{\circ}\text{C}$ under the C-HTC process, average PSD extended up to 1,200 μm . When comparing the profile of raw SS to that of char obtained at 160 $^{\circ}\text{C}$ from both processes, a striking difference – characterized by a ‘swelling effect’ – can be seen. The effect is consistent with the disintegration/ fragmentation of solids, as observed in previous studies (Chen *et al.* 2011; Chen *et al.* 2012). Subsequent increases in temperature to 180 $^{\circ}\text{C}$ and 200 $^{\circ}\text{C}$ show the cumulative volume distribution profiles shifting towards a proliferation of smaller and finer particles – characterized by a ‘swell-rupture effect’. Comparatively, however, M-HTC appears to result in an increase in solid fragmentation and solubilization compared to C-HTC, especially at 180 $^{\circ}\text{C}$. This further supports results obtained during dewaterability studies. These data further illustrate an increase in fragmentation of raw SS solids with increasing temperature, indicating that increased solid particle solubilization is a function of reaction temperature.

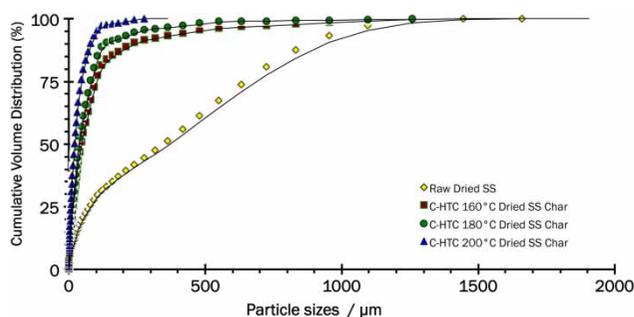


Figure 2 | PSD profiles of raw SS and chars from C-HTC process.

The significant reduction in particle size from both processes with increasing temperature when compared with raw SS is made clearer by the D10, D50 and D90 distribution of chars recovered at the three HTC temperature ranges compared to raw SS, as shown in Table 3.

Using the cut-off diameter D90, raw SS was 876 μm compared to those obtained from M-HTC and C-HTC at 160 $^{\circ}\text{C}$ of 232 μm and 227 μm respectively. This correlates with CST values of raw SS and CST values for chars obtained at 160 $^{\circ}\text{C}$. At 180 $^{\circ}\text{C}$ and 200 $^{\circ}\text{C}$, D90 values decreased significantly to <90 μm and <130 μm for the M-HTC and C-HTC process respectively, in contrast to raw SS and chars obtained at 160 $^{\circ}\text{C}$. This further illustrates why dewaterability was promoted by temperatures greater than 160 $^{\circ}\text{C}$, although there appears to be no substantial benefit of raising the temperature above 180 $^{\circ}\text{C}$. The same trends were observed at D10 and D50 respectively across the two HTC processes, and at all other temperatures used. Comparatively, M-HTC indicated lower D50 and D90 values for char recovered at 180 $^{\circ}\text{C}$ and 200 $^{\circ}\text{C}$ than those from the C-HTC process.

Effectively, both C-HTC and M-HTC heating methods behaved similarly; i.e. they initiated breakdown of solid aggregates and facilitated the removal of smaller particles of solids, while increasing HTC temperature further enhanced the fragmentation and solubilization of solid aggregates. This explains why the carbonized solids from both processes are more friable and easily ground into homogeneous powders after drying than the dried starting

Table 3 | D10, D50 and D90 distribution of raw SS and carbonized chars from both HTC processes

Sample description	Diameter size (μm)		
	D10	D50	D90
Raw SS	17.1	347.4	875.8
M-HTC 160 $^{\circ}\text{C}$ dried SS char	4.8	52.7	232.2
M-HTC 180 $^{\circ}\text{C}$ dried SS char	3.9	31.9	88.2
M-HTC 200 $^{\circ}\text{C}$ dried SS char	2.3	19.8	78.7
C-HTC 160 $^{\circ}\text{C}$ dried SS char	4.2	44.3	227.3
C-HTC 180 $^{\circ}\text{C}$ dried SS char	3.5	36.6	129.3
C-HTC 200 $^{\circ}\text{C}$ dried SS char	3.3	25.2	80.9

Where:

D10 – represents the particle size (μm), where 10% of sample particle sizes are less (smaller) than this value and 90% are greater (larger) than this value.

D50 – represents the median particle size (μm), where 50% i.e. half of sample particle sizes are less (smaller) than this value and the other half are greater (larger) than this value.

D90 – represents the particle size (μm), where 90% of sample particle sizes are less (smaller) than this value and 10% are greater (larger) than this value.

materials. Hence, both processes can convert raw SS into chars amenable to grinding and powdering for moulding into high-density pellets for fuel, for example. However, the PSD profiles of chars from both HTC methods suggest fragmentation, and particle size reduction/re-distribution largely affected by the HTC temperature used. The microwave heating mechanism, though, may have accounted for the increased fragmentation, smaller and finer particles being observed for chars recovered from the M-HTC process, as exposure to increasing energetic microwave irradiation tends to make particles become smaller and smaller due to the continuous frictions/attrition occurring between molecules of already degraded/disrupted sludge flocs and broken sludge cell structures (Chang *et al.* 2011).

Value recovery and consumptive energy audit

Table 4 shows the char yield, concentration of ammonia in recovered liquor and energy consumption by both processes. Generally, depending on the type and characteristics (among other factors) of the feedstock, an average 50–80% in char yield is typical of HTC processes within temperature ranges of 180–250 °C, regardless of the heating source (Funke & Ziegler 2010; Libra *et al.* 2011). Different yields are also characteristic of different feedstock properties, with moisture content and percentage solid loading being crucial (Ramke *et al.* 2009; Masek *et al.* 2013). Char yield recovered from both processes in this study are within these ranges, as shown in Table 4. The effects of carbonization temperature on char yield from both processes are similar, i.e. char yield from both processes decreased with increasing temperature of carbonization. This supports the proposition of fragmentation and solubilization during the HTC process increasing with carbonization temperature, while char yield decreases. Net decreases in char yield over the temperature investigated were 10.8% and 14.1% for the M-HTC and C-HTC processes respectively.

Up to 1.4 g/l of ammonia was recovered from both processes. The concentration of ammonia recovered was

observed to increase with temperature, and this result is similar to previous studies (Lian-hai *et al.* 2006; Wilson & Novak 2009; Sun *et al.* 2013). Basically, protein and other nitrogenous compounds are the primary sources of nitrogen in the raw HBW. At temperatures greater than 150 °C, these compounds are hydrolyzed and decomposed to amino acids, organic-N and ammonium compounds. With increasing temperature (≥ 180 °C), deamination and hydrolysis of amino acids into short-chain VFA, ammonia and carbon IV oxide occurs (Lian-hai *et al.* 2006; Sun *et al.* 2013), which further illustrates the increasing concentration of ammonia recovered as the temperature increased to 200 °C. Comparatively, while both processes tend to produce similar char yields, the C-HTC recovered a slightly higher concentration of ammonia at 180 °C and 200 °C than the M-HTC process. This may be due to the longer residence of the C-HTC process. The level of ammonia in the liquor phase from both processes supports the proposition that this may be used as liquid fertilizer. Ammonia recovery may be seen as an apparent additional economic benefit from HBW management using the HTC process. However, the direct use in agriculture requires further assessment, and other factors, such as endocrine-disrupting exogenous compounds and heavy metals, which are beyond this study, ought to be considered.

When the overall energy required for processing raw SS into value-added char and ammonia in recovered liquor is taken into account, the C-HTC process consumed significantly more energy than the M-HTC process, as shown in Table 4. Energy required to process raw SS solids using the C-HTC process at every other temperature considered almost doubles that required for M-HTC, despite the relatively small differences in the char recovered and ammonia in recovered liquor from both processes. Additionally, and as expected, energy consumption increased with increasing temperature; however, the C-HTC process consumed more with increasing temperature than M-HTC. For example, increasing temperature from 160 to 200 °C for SS increased energy consumption by 19.73 Wh·g⁻¹ TS for M-HTC and 84 Wh·g⁻¹ TS for the C-HTC process.

Table 4 | Comparative energy consumption and char yield from both HTC methods

Temperature (°C)	Energy consumed (Wh·g ⁻¹ TS)		Char yield (%)		Ammonia in recovered liquor (g/l)	
	M-HTC	C-HTC	M-HTC	C-HTC	M-HTC	C-HTC
160	103.6 ± 0.6	194.9 ± 0.1	61.3 ± 1.2	60.2 ± 1.8	0.7 ± 0.04	1.1 ± 0.02
180	114.2 ± 0.4	267.6 ± 0.3	54.4 ± 1.6	52.4 ± 1.1	0.9 ± 0.05	1.2 ± 0.03
200	123.3 ± 0.1	279.3 ± 0.5	50.5 ± 0.9	46.1 ± 0.8	1.2 ± 0.03	1.4 ± 0.04

The higher energy consumption associated with the C-HTC process as compared with M-HTC is due to the average processing time (hrs) required for each process to achieve carbonization. In this study, average processing time includes the warming time to peak temperature and residence time at that temperature. The M-HTC process takes 15 mins to attain peak temperature and 30 mins as minimum residence times to achieve carbonization; hence the 0.75 hrs average processing/conversion time from raw SS to chars. The C-HTC process takes 2 hrs to attain peak temperature and a minimum of 3 hrs to ensure enough contact time for carbonization to occur. Based on average processing time involved to achieve carbonization from both processes in this study, the average raw SS solids processing rate, g (TS)/hr, were 9.39 and 1.41 for M-HTC and C-HTC respectively. Hence the M-HTC process has a higher process-conversion efficiency of raw SS into valuable char by a factor of six, and consumes less energy when compared with the C-HTC process. This is similar to the conclusion of previous studies (Chang *et al.* 2011; Gronnow *et al.* 2013) that have identified the microwave process as being more efficient for converting biomass into chars.

These data clearly demonstrate that both HTC temperature and heating method affect raw SS process-conversion efficiency to char. While both processes behaved similarly in terms of char yield and concentrated ammonia recovered in liquor with increasing carbonization temperature, the disparities in SS conversion/processing rate and energy consumption can be attributed to differences in the heating mechanisms between the processes. The C-HTC process transfers heat energy to material by convection and conduction from the heating source via thermal gradients to the core of the processed material inside the reactor. By contrast, the M-HTC process occurs at the molecular level via direct interaction of high frequency electromagnetic radiation with dipolar molecules (water, proteins and other liquid constituents of wet HBW), which cause dielectric heating from molecular rotation and vibrations. This in effect leads to enhanced selectivity, homogenous and volumetric heating throughout the raw SS inside the microwave reactor, which consequently leads to a faster process via novel reaction pathways, potentially due to reduced activation energy (Sobhy & Chaouki 2010; Yin 2012). The merit of the shorter processing time of raw SS and higher recovery rate of chars associated with microwave processing further implies higher throughput potential, and this may represent a significant advantage over the C-HTC process in terms of biowaste processing for value-added products recovery.

Chars and recovered liquor properties

The proximate, elemental analysis of carbon, hydrogen, nitrogen and oxygen, and the energy properties of chars and recovered liquor properties at each carbonization temperature from both HTC processes is presented in Table 5.

The TS of chars are greater than of raw SS (4.4%), this being consistent with decreased moisture content. Higher TS in chars is a typical characteristic of the HTC process, from the re-distribution of solids during the process. TS of chars were also observed to increase as carbonization temperature increased. The VS and FS of chars recovered from both HTC processes were similar in range: 59% to 67% and 32% to 41% respectively. While VS decreased with increasing carbonization temperature, FS appeared to increase with increasing carbonization temperature. The carbon content of chars recovered at each HTC temperature investigated was fairly stable at 38%, representing less than 3% increase over raw SS. The carbon densification factor, which indicates the ratio of carbon concentrated in chars (dry basis) compared with raw SS, was greater than 1 in all cases. Literature values for carbon densification range between 1 and 1.8 (Servilla & Fuertes 2009a, 2009b; Lu *et al.* 2013). Between 45.9% and 62% of carbon from starting SS was retained in recovered chars, and this range was similar to previous study findings on the carbon distribution in solid chars recovered from municipal waste and lignocellulosic substrates (Berge *et al.* 2011; Hoekman *et al.* 2011; Lu *et al.* 2012). However, carbon retained in recovered char decreased with increasing HTC temperature investigated due to C-content solubilization. The amount of carbon sequestered in chars after HTC was estimated as the carbon storage factor (CSF). CSF represents the mass equivalence of carbon remaining in char solids per unit dry mass of raw feedstock after biological decompositions in a landfill (Barlaz 1998). This factor provides a means for a relative comparison of sequestered carbon. Table 5 shows that CSF values ranged between 0.19 and 0.25 from both methods. CSF was also observed to decrease slightly as the temperature increased from 160 °C to 200 °C. Previously reported CSF values for paper, food, municipal solid waste and anaerobic digested wastes were 0.18, 0.34, 0.23 and 0.14 respectively (Lu *et al.* 2012). Comparatively, these ranges are very similar to those reported in this study. High CSF values could imply a potentially long-term stability of carbon sequestered in chars if disposed or used in agriculture; however, this is still largely unknown and requires further investigation.

Table 5 | Properties of chars and liquor recovered from both HTC process

	M-HTC			C-HTC		
	160 °C	180 °C	200 °C	160 °C	180 °C	200 °C
Solid char						
Proximate analysis (%)						
TS	10.8 ± 0.1	11.4 ± 0.3	12.9 ± 0.2	10.3 ± 0.2	10.9 ± 0.1	12.7 ± 0.2
VS	65.5 ± 2.1	62.6 ± 1.1	58.6 ± 0.7	67.1 ± 0.3	62.9 ± 0.9	59.2 ± 0.0
FS	34.5 ± 1.9	37.4 ± 1.3	41.4 ± 0.6	32.9 ± 0.2	37.1 ± 0.7	40.8 ± 0.8
Elemental analysis (%)						
C	38.1 ± 0.4	38.0 ± 0.1	38.2 ± 0.2	39.2 ± 0.1	38.8 ± 0.3	37.9 ± 0.7
H	5.2 ± 0.04	5.1 ± 0.02	5.0 ± 0.02	5.5 ± 0.09	5.1 ± 0.04	4.8 ± 0.05
N	3.6 ± 0.03	3.2 ± 0.1	2.6 ± 0.03	3.4 ± 0.08	3.0 ± 0.02	2.8 ± 0.01
O ^a	53.1 ± 0.5	53.7 ± 0.2	54.2 ± 0.2	51.9 ± 0.3	53.1 ± 0.4	54.5 ± 0.8
Carbon properties						
C _{DF} ^b	1.04	1.03	1.04	1.07	1.06	1.04
C _{RW} ^c	61.4	54.4	50.7	62.0	53.5	45.9
CSF ^d	0.23	0.21	0.19	0.25	0.22	0.19
Energy properties						
HHV (MJ/kg)	16.8 ± 0.6	16.4 ± 0.2	16.8 ± 0.3	16.7 ± 0.1	16.2 ± 0.4	16.3 ± 0.3
EEF ^e	1.06	1.04	1.06	1.06	1.03	1.03
E _Y (%) ^f	64.9	56.6	53.5	63.8	53.9	47.4
Liquor						
pH	4.39	4.81	4.86	4.85	4.91	5.07
TOC (g/l)	9.3 ± 0.2	9.7 ± 0.1	10.3 ± 0.4	9.6 ± 0.3	10.3 ± 0.5	9.9 ± 0.4
COD (g/l)	30.8 ± 0.8	31.5 ± 0.5	32.3 ± 0.6	34.1 ± 0.4	35.6 ± 0.1	36.8 ± 0.6
VFA (g/l)	7.1 ± 0.01	6.2 ± 0.02	5.7 ± 0.3	7.0 ± 0.1	5.3 ± 0.2	4.9 ± 0.2

^aDetermined by difference, i.e. [100-(C + H + N)]%.

^bCarbon densification factor, $C_{DF} = \frac{\% \text{ carbon in dried char solids}}{\% \text{ carbon in dried raw SS}}$.

^c%Weighted carbon retained in chars from raw, $C_{RW} = \frac{(\% \text{ carbon in dried char solids} \times \text{mass of dried char recovered})}{(\% \text{ carbon in dried raw SS} \times \text{mass of dried raw SS})}$.

^dCSF = $\frac{\text{Mass of carbon in char}}{\text{Mass of dried raw biowaste}}$

^eEEF = $\frac{\text{HHV of dried chars solids}}{\text{HHV of dried raw SS}}$.

^fEnergy yield, $E_Y(\%) = \text{EEF} \times \text{char yield}(\%)$.

The HHV is one of the most important characteristics of chars regarding their potential use as solid fuel. The calorific value also enables the estimation/assessment of key energetic parameters such as energy densification and energy yield for comparative assessment with both raw SS and conventional fuels. The effect of HTC temperature and heating methods on raw SS was observed to generate chars with calorific value improvement up to 16.8 MJ/kg, greater than low-rank fuels such as peat (13.8–15.4 MJ/kg), comparable to lignite (16.3–16.9 MJ/kg) and close to some grades of bituminous coal (17 MJ/kg) (Haykiri-Açma *et al.* 2002; Speight 2005; Haykiri-Açma & Yaman 2010). Similar

observations have been reported in many studies, with many substrates and heating sources (Hoekman *et al.* 2011; Chen *et al.* 2012; Parshetti *et al.* 2013). The energy content of chars recovered from wastewater sludge ranges from 14.4 to 27.2 MJ·kg⁻¹ (Ramke *et al.* 2009; Ozcimen & Ersoy Mericboyu 2010; Lu *et al.* 2011; Berge *et al.*, 2011). These are comparable to the HHVs obtained for all chars recovered in this study. During HTC carbonization, the solid mass decreases due to solubilization and this results in energy densification – as indicated by the energy enrichment factor (EEF) i.e. the ratio of the HHV of char to raw SS. In Table 5, the EEF of all chars recovered from raw

SS was greater than 1 in all cases. Both processes yield energy densification factors comparable to previous-reported HTC studies specifically run to enhance energy densification on a variety of feedstocks (Hwang *et al.* 2012; Roman *et al.* 2012). This is evidence that both HTC processes appear to promote energy densification in chars. Energy yield provides a means for assessing the energy recoverable from chars. Consistent with similar studies, energy yields decreases gradually with increasing carbonization temperature – primarily due to reducing char yield. Increasing temperature from 160 to 200 °C resulted in a corresponding decrease in energy yield by 11% and 16% from the M-HTC and C-HTC processes respectively. Measured independently, carbon densification and EEF values are in agreement, which reflect the relationships between carbon content and heating value of the chars. N-content in raw SS decreased when compared to those recorded in recovered chars, as seen in Table 5, due to thermolytic flushing of N-content in raw SS into the liquid phase during the HTC process. This increased with increasing temperature and was consistent with the increase in ammonia concentration in the liquor recovered. The low N-content in chars will further reduce the amount of unwanted nitrogen oxides during combustion, reducing the environmental impact.

The properties of liquor measured across the temperature ranges studied in this work suggest similarity in values and trends for both HTC methods, with HTC temperature largely affecting measured values. The pH of the liquor was generally slightly acidic, and increased slightly with increasing HTC temperature. This is consistent with VFA values, which decreased with increasing temperature. Increasing decomposition of organic acids or volatilization of intermediate organic compounds with increasing temperature may be responsible for observations associated with decreasing VFA values. Similarly, both TOC and COD values generally tend to increase with increasing temperature for both HTC methods. This is because in the presence of sub-critical water, polysaccharides (the primary source of C-content in HBW) are broken down and enhanced in dissolution rates into the liquid phase as HTC temperatures increases. This ultimately aids the absolute carbon loss per unit mass of raw HBW to the liquid phase, as revealed by the COD values.

CONCLUSION

The potentials of conventional and M-HTC processes (under three temperature regimes) for treating/processing HBW,

while recovering value-added solid char fuel and liquor rich in ammonia, is demonstrated and comparatively evaluated in this paper. No doubt, both parameters i.e. HTC source of heating and temperature investigated, are important for the conversion of HBW and recovery of valuable end products. While both processes compare in yield, carbon and energetic properties of char and recovered liquor, differences were observed in dewaterability, PSD and energy use. They both produced chars of lower PSD, 70–130 µm (using D90 as the cut-off diameter) when compared with raw SS, yet with improved CST values corresponding to improved sludge dewaterability. Based on this study, the potential merits of M-HTC over the C-HTC process in terms of biowaste-processing efficiency include:

- faster processing times, due to rapid volumetric heating;
- higher processing rates, due to the relatively lower residence time required;
- a better dewaterability rate, due to the thermal and athermal effects of microwave heating;
- the lower energy requirement to convert SS into valuable end products (chars and ammonia liquor) at all temperatures; and
- potential recovery of char yields slightly higher than for the C-HTC process, despite higher energy consumption and processing time.

ACKNOWLEDGEMENTS

The authors would like to thank The Bill & Melinda Gates Foundations for funding Loughborough University, UK, on the ‘Reinvent the Toilet Challenge’ project. The views expressed in this paper are of the authors. Mr Geoff Russell is greatly appreciated for his assistance in collection of primary SS from the wastewater treatment plant.

REFERENCES

- Afolabi, O. O. D., Sohail, M. & Thomas, C. P. L. 2015 *Microwave hydrothermal carbonization of human biowastes*. *Waste Biomass Valorisation* **6**, 147–157.
- APHA/AWWA/WEF 2005 *Standard Methods for the Examination of Water and Wastewater*, 21st edn. American Public Health Association/American Water Works Association/Water Environment Federation, Washington, DC, USA.
- ASTM D5373-16 *Standard Test Methods for Determination of Carbon, Hydrogen and Nitrogen in Analysis Samples of Coal and Carbon in Analysis Samples of Coal and Coke*. ASTM International, West Conshohocken, PA, USA.

- Barlaz, M. A. 1998 Carbon storage during biodegradation of municipal solid waste components in laboratory-scale landfills. *Global Biochemical Cycles* **12** (2), 373–380.
- Basso, D., Weiss-Hortala, E., Patuzzi, F., Castello, D., Baratieri, M. & Fiori, L. 2015 Hydrothermal carbonization of off-specification compost: a byproduct of the organic municipal solid waste treatment. *Bioresource Technology* **182**, 217–224.
- Basso, D., Patuzzi, F., Castello, D., Baratieri, M., Rada, E. C., Weiss-Hortala, E. & Fiori, L. 2016 Agro-industrial waste to solid biofuel through hydrothermal carbonization. *Waste Management* **47** (1), 114–121.
- Berge, N. D., Ro, K. S., Mao, J., Flora, J. R. V., Chappell, M. A. & Bae, S. 2011 Hydrothermal carbonisation of municipal waste streams. *Environment Science and Technology* **45**, 5696–5703.
- Chang, C.-J., Tyagi, V. K. & Lo, S.-L. 2011 Effects of microwave and alkali induced pretreatment on sludge solubilization and subsequent aerobic digestion. *Bioresource Technology* **102**, 7633–7640.
- Chen, W. H., Tu, Y. & Sheen, H.-K. 2011 Disruption of sugarcane bagasse lignocellulosic structure by means of dilute sulfuric acid pretreatment with microwave-assisted heating. *Applied Energy* **88**, 2726–2734.
- Chen, W., Ye, S. & Sheen, H.-K. 2012 Hydrothermal carbonisation of sugarcane bagasse via wet torrefaction in association with microwave heating. *Bioresource Technology* **118**, 195–203.
- Eliagwu, S. E. & Greenway, G. M. 2016 Microwave-assisted hydrothermal carbonization of rapeseed husk: a strategy for improving its solid fuel properties. *Fuel Processing Technology* **149**, 305–312.
- Eskicioglu, C., Terzian, N., Kennedy, K. J., Droste, R. L. & Hamoda, M. 2007 Athermal microwave effects for enhancing digestibility of waste activated sludge. *Water Research* **41**, 2457–2266.
- Esrey, S. 2001 Towards a recycling society: ecological sanitation – closing the loop to food security. *Water Science and Technology* **43** (4), 177–187.
- Funke, A. & Ziegler, F. 2010 Hydrothermal carbonization of biomass: a summary and discussion of chemical mechanisms from process engineering. *Biofuels, Bioproduction and Biorefinery* **4** (2), 160–177.
- Gronnow, M. J., Budarin, V. L., Masek, O., Crobie, K. N., Brownsort, P. A., Shuttleworth, P. S., Hurst, P. R. & Clark, J. M. 2013 Torrefaction/biochar production by microwave and conventional slow pyrolysis – comparison of energy properties. *Global Change Biology Bioenergy* **5**, 144–152.
- Guiotoku, M., Rambo, C. R., Hansel, F. A., Magalhaes, W. L. E. & Hotza, D. 2009 Microwave-assisted hydrothermal carbonization of lignocellulosic materials. *Materials Letters* **63**, 2707–2709.
- Guiotoku, M., Rambo, C. R., Maia, C. M. B. F. & Hotza, D. 2011 Synthesis of carbon-based materials by microwave-assisted hydrothermal process. In: *Microwave Heating* (U. Chandra, ed.). Intech, New York, USA, pp. 291–308.
- Haykiri-Açma, H. & Yaman, S. 2010 Interaction between biomass and different rank coals during co-pyrolysis. *Renewable Energy* **35** (1), 288–292.
- Haykiri-Açma, H., Ersoy-Meriçboyu, A. & Küçükbayrak, S. 2002 Combustion reactivity of different rank coals. *Energy Conversion and Management* **43** (4), 459–465.
- Hoekman, S. K., Broch, A. & Robbins, C. 2011 Hydrothermal carbonisation of lignocellulosic biomass. *Energy Fuels* **25**, 1802–1810.
- Hwang, I. H., Aoyama, H., Matsuto, T., Nakagishi, T. & Matsuo, T. 2012 Recovery of solid fuel from municipal solid waste by hydrothermal treatment using subcritical water. *Waste Management* **32**, 410–416.
- ISO 13320 2009 *Standard Method Particle Size Analysis – Laser Diffraction Method*. ISO, Geneva, Switzerland.
- ISO 1928 2009 *Solid Mineral Fuels – Determination of Gross Calorific Value by the Bomb Calorimetric Method, and Calculation of net Calorific Value*. ISO, Geneva, Switzerland.
- Langergraber, G. & Muellegger, E. 2005 Ecological sanitation – a way to solve global sanitation problems? *Environment International* **31**, 433–444.
- Lian-hai, R., Yong-feng, N., Jian-guo, L., Yi-ying, J. & Lu, S. 2006 Impact of hydrothermal process on the nutrient ingredients of restaurant garbage. *Journal of Environmental Science* **18**, 1012–1019.
- Libra, J. A., Ro, K. S., Kammann, C., Funke, A., Berge, N., Neubauer, Y., Titirici, M., Fuhner, C., Bens, O., Kern, J. & Emmerich, K. 2011 Hydrothermal carbonization of biomass residuals: a comparative review of the chemistry, processes and applications of wet and dry pyrolysis. *Biofuels* **2** (1), 89–124.
- Lu, L., Namioka, T. & Yoshikawa, K. 2011 Effects of hydrothermal treatment on characteristics and combustion behaviours of municipal solid wastes. *Applied Energy* **88**, 3659–3664.
- Lu, X., Jordan, B. & Berge, N. D. 2012 Thermal conversion of municipal solid waste via hydrothermal carbonisation: comparison of carbonization products to products from current waste management techniques. *Waste Management* **32**, 1353–1365.
- Lu, X., Pellechia, P. J., Flora, J. R. V. & Berge, N. D. 2013 Influence of reaction time and temperature on product formation and characteristics associated with the hydrothermal carbonisation of cellulose. *Bioresource Technology* **138**, 180–190.
- Mäkelä, M., Benavente, V. & Fullana, A. 2015 Hydrothermal carbonization of lignocellulosic biomass: effect of process conditions on hydrochar properties. *Applied Energy* **155**, 576–584.
- Masek, O., Budarin, V., Gronnow, M., Crombie, K., Brownsort, P., Fitzpatrick, E. & Hurst, P. 2013 Microwave and slow pyrolysis biochar: comparison of physical and functional properties. *Journal of Analytical and Applied Pyrolysis* **100**, 41–48.
- Neyens, E. & Baeyens, J. 2003 A review of thermal sludge pre-treatment processes to improve dewaterability. *Journal Hazardous Materials* **98** (1–3), 51–67.
- Nurtsen, H. 2005 *The Maillard Reaction: Chemistry, Biochemistry and Implications*. RSC, Cambridge.
- Ozcimen, D. & Ersoy Mericboyu, A. 2010 Characterisation of biochar and bio-oil samples obtained from carbonisation of various biomass materials. *Renewable Energy* **35**, 1319–1324.

- Parshetti, G. K., Hoekman, S. K. & Balasubramanian, R. 2013 Chemical, structural and combustion characteristics of carbonaceous products obtained by hydrothermal carbonisation of palm empty fruit bunches. *Bioresource Technology* **135**, 683–689.
- Peterson, A. A., Vogel, F., Lachance, R. P., Froeling, M. & Antal, M. J. 2008 Thermochemical biofuel production in hydrothermal media: a review of sub-and supercritical water technologies. *Energy and Environmental Science* **1**, 32–65.
- Peterson, A. A., Lachance, R. P. & Tester, J. W. 2010 Kinetic evidence of the Maillard reaction in hydrothermal biomass processing: glucose-glycine interactions in high-temperature, high-pressure water. *Industrial and Engineering Chemistry Research* **49**, 2107–2117.
- Pino-Jelcic, S. A., Hong, S. M. & Park, J. K. 2006 Enhanced anaerobic biodegradability and inactivation of fecal coliforms and *Salmonella* spp. in wastewater sludge by using microwaves. *Water Environment Research* **78**, 209–216.
- Ramke, H. G., Blohse, D., Lehmann, H. J. & Fettig, J. 2009 Hydrothermal carbonisation of organic waste. In: *Proceedings of Twelfth International Waste Management and Landfill Symposium, Sardinia, Italy*, 5–9 October 2009, CISA publisher.
- Roman, S., Nabais, J. M. V., Laginas, C., Ledesma, B. & Gonzalez, J. F. 2012 Hydrothermal carbonisation as an effective way of densifying the energy content of biomass. *Fuel Processing Technology* **103**, 78–83.
- Samolada, M. C. & Zabaniotou, A. A. 2014 Comparative assessment of municipal sewage sludge incineration, gasification and pyrolysis for a sustainable sludge-to-energy management in Greece. *Waste Management* **34** (2), 411–420.
- Servilla, M. & Fuertes, A. B. 2009a Chemical and structural properties of carbonaceous products obtained by hydrothermal carbonisations of saccharides. *Chemistry European Journal* **15**, 4195–4203.
- Servilla, M. & Fuertes, A. B. 2009b The production of carbon materials by hydrothermal carbonisation of cellulose. *Carbon* **47**, 2281–2289.
- Sobhy, A. & Chaouki, J. 2010 Microwave-assisted bio-refinery. *Chemical Engineering Transactions* **19**, 25–30.
- Sobsey, M. D. 2006 *Excreta and household wastewaters – introduction*. Global Water, Sanitation and Hygiene. ENVR 890 section 003, ENVR 296 section 003.
- Solymon, K., Mato, R. B., Perez-Elvira, S. I. & Cocero, M. J. 2011 The influence of the energy from microwave pretreatment on biogas production from secondary wastewater sludge. *Bioresource Technology* **102**, 10849–10854.
- Speight, J. G. 2005 *Handbook of Coal Analysis*. Wiley Interscience, Hoboken, NJ, USA.
- Strauss, M. & Montangero, A. 2002 *Faecal Sludge Management: Review of Practises, Problems and Initiatives*. EAWAG/SANDEC Publications, Switzerland.
- Sun, X. H., Sumida, H. & Yoshikawa, K. 2013 Effects of hydrothermal process on the nutrient release of sewage sludge. *International Journal of Waste Resources* **3**, 124.
- WHO/UNICEF 2014 *Progress on Sanitation and Drinking Water. Update*. World Health Organization, Geneva.
- Wilson, C. A. & Novak, J. T. 2009 Hydrolysis of macromolecular components of primary and secondary wastewater sludge by thermal hydrolytic pre-treatment. *Water Research* **43**, 4489–4498.
- Wojciechowska, E. 2005 Application of microwaves for sewage sludge conditioning. *Water Research* **39**, 4749–4754.
- Xun, R., Wang, W., Qiao, W. & Yin, K. 2008 Status of urban sludge treatment and hydrothermal reduction technology of enhanced dewatering. *Environmental Sanitation Engineering* **16**, 28–32.
- Yin, C. 2012 Microwave-assisted pyrolysis of biomass for liquid biofuel production. *Bioresource Technology* **120**, 273–284.

First received 25 October 2016; accepted in revised form 6 March 2017. Available online 18 March 2017